

Effect of Hygrothermal Loading on Laminate Composites

A. Deepa^{1*}, K. Padmanabhan¹ and G. Raghunadh²

¹SMEC, VIT University, Vellore - 632014, Tamil Nadu, India; deepa.a@vit.ac.in, padmanabhan.k@vit.ac.in

²School of Mechanical Engineering, VIT University, Vellore - 632014, Tamil Nadu, India; sairaghunadh@gmail.com

Abstract

Objective: To find the effect of hygrothermal loading on CFRP and GFRP composite materials by finding the properties like capacitance, micro hardness, moisture diffusivity and area of fraction. **Methods:** Hand layup and vacuum bag methods were used for fabrication of composites. **Finding:** Three-point bending test was done on each specimen by varying load, i. e, zero load, with 30% load, 50% load and 70% load for different time periods. Micro hardness and capacitance were determined using Vickers Hardness tester and LCR meter respectively on both the composites before and after the thermal treatment. The capacitance increased with time whereas the percentage area of fraction of the fibre decreased. Also, the reduction in strength and damage to fibre were investigated using SEM. It was observed that with increase in %weight gain, micro hardness of specimen decreased. **Application/Improvement:** FRPs can substitute traditional steel reinforcements in reinforced concrete structures. The continuous loading under thermal actions due to natural environmental factors lead to degrading effect that needs to accurate investigations in evaluating durability of fibre reinforced polymers.

Keywords: Area of Fraction, Capacitance, Failure Modes, Hygrothermal Loading, Micro Hardness

1. Introduction

Composite materials are the engineered made up of two or more constituent materials with different mechanical properties. The final product has properties higher than that of individual components. It is a combination of two materials matrix phase and reinforcement phase, matrix is a continuous phase usually more ductile and holds the reinforced phase dispersed in it and both shares the load applied. Different materials are obtained by changing the matrix and reinforced phases. The material mentioned in this paper is made by FRP as reinforced phase and epoxy as matrix phase. The main benefits of composites is that, less weight, high strength-to-weight ratio, directional stiffness and surface properties like corrosion resistance etc. made to use composites in almost every field of engineering including aerospace applications. Delamination is the major type of failure^{1,2}. As the FRP material is concerned, the environmental factors like moisture, temperature, heat or radiation from surroundings has a great impact on the degradation^{3,4} of the material. The present study

deals with impact of hygrothermal loading^{5,6} on FRP materials^{7,8}, this effect is calculated by using capacitance, impedance values and by calculating molecular diffusivity. The specimens are fabricated according to ASTM standards^{9,10} and is kept in a water bath maintained at a temperature^{11,12} and is taken out at regular interval of time and is tested, readings are tabulated. Firstly, the material is pre conditioned and ultimate load is determined using UTM and 30%, 50% and 70% of ultimate load is applied, for both hygrothermally placed material¹³ and normal material, results are compared in both the cases. The reasons behind the decrease or increase in properties are discussed.

2. Experimentation and Fabrication of Specimen

Specimens are made by using commercially available GFRP and CFRP sheets and placed along 0° orientation side for cutting purpose. In order to decide the specifica-

*Author for correspondence

tions, ASTM standard D3037/3039 and D790 were used and mentioned in Table 1.

Table 1. Specimen specifications used for testing

S. No	Specification of the Specimen	For tensile testing(mm)	For bending test (mm)
1.	Length	500	250
2.	Width	15	15
3.	Thickness	3 (for GFRP) & 4.32 (for CFRP)	3 (for GFRP) & 4.32 (for CFRP)

The specimens are placed in water bath and maintained at a temperature (45°) and at regular interval of time as mentioned in the preceding tabular columns, specimen is taken out and test are done accordingly.

3. Testing Methods Used

3.1 Tensile Testing

A UTM is used for the testing the tensile strength of the specimen and prepared according to ASTM-D-3039 standard. Initial pre stretching is done, (shown in Figure 1) peak load is calculated i.e., ultimate stress value that the specimen can with stand.



Figure 1. Tensile laminate composite.

3.2 Capacitance Test

In order to relate the moisture absorption rate with capacitance, the capacitance and impedance readings from RCL meter are used (shown in Figure 2). To create magnetic field in the specimen copper strips were used as terminals.



Figure 2. LCR meter.

3.3 Micro Hardness Test

To estimate the hardness of the specimen before and after thermal treatment micro hardness test is used. A load of 200gm is applied and VHN values were determined by applying this load and dwell time used while applying load is 20 sec. A diamond shaped indent is formed as shown in Figure 3.

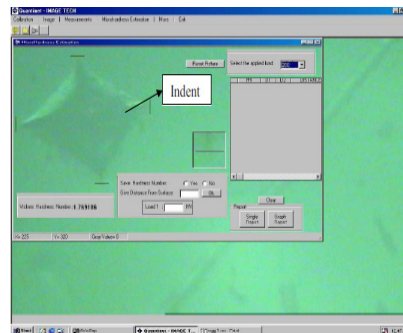


Figure 3. Indent of the specimen.

3.4 SEM (Scanning Electron Microscopy)

To find the micro structure of the specimen scanning electron microscope is used and polishing is done by gold coating equipment and microstructure is obtained at magnification factor of 2000X and 1500X.

4. Failure Modes in Composites

Delamination and fibre pull-out are the failure mechanisms in composite materials. Delamination is an insidious kind of failure and it develops inside of the material (Figure 4) and it may be detected in a material by its sound. Delaminated part sounds fewer dull compared to solid composite which give more sound. Non-destructive testing may also be used to determine the failure in composites which include ultrasonic, radiographic and infrared imaging.

5. Percentage Weight Gain

The pre conditioned sample is weighed periodically and ensure that moisture on the surface is wiped before weighing. Weight gain is determined as follows

$$\%W = \frac{W_1 - W_2}{W_2}$$

where,

%W is weight gain percentage in specimen

W_1 is weight of specimen

W_2 is weight of dry specimen

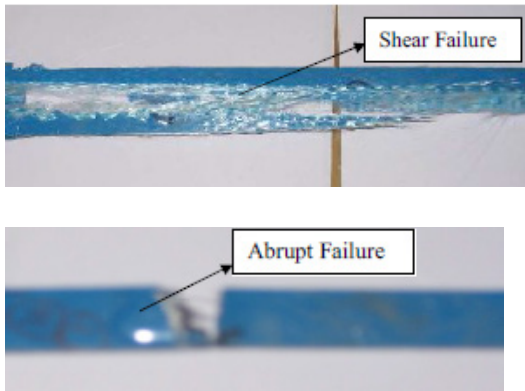


Figure 4. Failure of CFRP and GFRP laminates after 1 month.

6. Calculation of Apparent Moisture Diffusivity

Assuming that the moisture absorption follows Frick's law, the diffusivity D can be calculated as,

$$D = \pi \left(\frac{h}{4M_m} \right)^2 \left(\frac{M_2 - M_1}{\sqrt{t_2} - \sqrt{t_1}} \right) \left(1 + \frac{h}{L_e} + \frac{h}{W} \right)^{-2}$$

where,

L_e - length of the specimen

W -width of specimen

M_1 -moisture content at time t_1

M_2 -moisture content at time t_2

M_m - %weight gain from above equation

7. Results and Discussion

The initial specimen had a fine and shiny epoxy coating, when loaded under uniaxial tensile load showed a broom type failure due to instant release of stored energy.

8. Moisture Diffusivity Results of Bending Laminate

The moisture diffusivity is compared for various loads (Tables 2 and 3) and is noted that the specimens kept in water-bath(T_2) for two months absorbed more moisture than that of specimens of first month in almost all the specimens. The reason behind the decrease in moisture diffusivity is that, Weight gain of specimen increases with time for a given hygrothermal load giving way to moisture. The moisture diffusivity in GFRP is almost same as

shown in Figure 6. The range of moisture diffusivity values of CFRP (Figure 5) specimens were low compared to GFRP as shown in Figure 6.

Table 2. Moisture diffusivity of GFRP

Time period	GFRP 30% loading	GFRP 50% loading	GFRP 70% loading	GFRP without load
3	0.0113	0.0109	0.0110	0.0112
6	0.0055	0.0055	0.0055	0.0056
9	0.0036	0.0036	0.0037	0.0037
10	0.0063	0.0061	0.0059	0.0060
12	0.0027	0.0027	0.0027	0.0028
20	0.0018	0.0017	0.0016	0.0014
30	0.0011	0.0010	0.0010	0.0012
40	0.0009	0.0008	0.0009	0.0009
50	0.0014	0.0014	0.0013	0.0012

Table 3. Moisture diffusivity in CFRP laminated specimen

Time period	CFRP 30% loading	CFRP 50% loading	CFRP 70% loading	CFRP without load
3	0.007	0.020	0.018	0.020
6	0.022	0.010	0.009	0.010
9	0.011	0.007	0.006	0.007
10	0.006	0.006	0.008	0.008
12	0.005	0.005	0.005	0.005
20	0.001	0.001	0.001	0.002
30	0.001	0.001	0.001	0.001
40	0.001	0.001	0.001	0.001
50	0.002	0.001	0.001	0.001

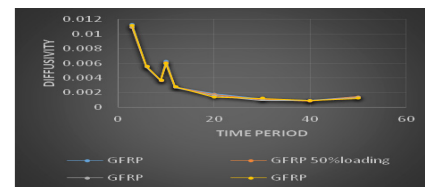


Figure 5. Graph for moisture diffusivity of GFRP.

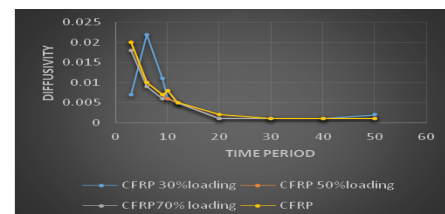


Figure 6. Graph for moisture diffusivity in CFRP.

9. LCR Meter Results of Bending Specimen

The capacitance of various loaded specimens (Tables 4, 5) are compared and is noted that capacitance increasing with respect to time indicating the degradation of the fibre. There is a marginal increase during early days but with course of time i.e. after 40 days in GFRP and 50 days in CFRP there is a marginal increase. The reason behind the increase in capacitance is that with time the %weight gain increases for a given hygrothermal load giving way to moisture. The capacitance of 30%loaded GFRP specimen has attained saturation before other specimen as shown in Figure 7, whereas for CFRP specimen started increasing after one month as it started gaining weight as shown in Figure 8.

Table 4. Capacitance results in GFRP laminated specimen

Time period	GFRP 30% loading	GFRP 50% loading	GFRP 70% loading	GFRP Without load
3	1.78E-11	2.90E-11	2.58E-11	2.08E-11
6	4.38E-11	3.35E-11	3.45E-11	2.59E-11
9	4.61E-11	3.60E-11	3.60E-11	2.63E-11
10	8.85E-11	3.73E-11	4.62E-11	3.42E-11
12	8.92E-11	3.99E-11	6.19E-11	3.58E-11
20	8.97E-11	5.31E-11	7.11E-11	3.69E-11
25	9.00E-11	6.12E-11	7.16E-11	4.79E-11
30	9.20E-11	7.04E-11	7.67E-11	6.95E-11
40	9.30E-11	7.74E-11	8.36E-11	7.52E-11
50	9.52E-11	8.51E-11	8.56E-11	9.13E-11

Table 5. Capacitance results in CFRP laminate specimen

Time period	CFRP 30% loading	CFRP 50% loading	CFRP 70% loading	CFRP Without load
3	1.03E-12	1.86E-12	3.40E-12	4.20E-13
6	2.04E-12	2.28E-12	3.60E-12	1.20E-12
9	2.60E-12	4.20E-12	4.36E-12	6.20E-12
10	4.82E-12	4.98E-12	5.30E-12	1.32E-11
12	5.10E-12	5.70E-12	7.40E-12	1.40E-11
20	5.70E-12	7.90E-12	9.80E-12	1.54E-11
25	1.24E-11	9.00E-12	1.86E-11	1.93E-11

30	1.75E-11	2.22E-11	2.89E-11	2.27E-11
40	1.94E-11	2.37E-11	4.63E-11	5.47E-11
50	3.50E-11	5.93E-10	5.58E-11	6.95E-11

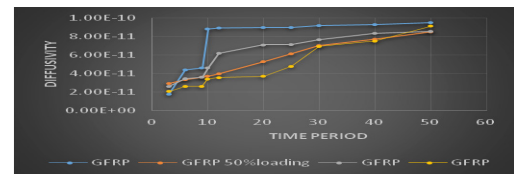


Figure 7. Graph for capacitance results in GFRP.

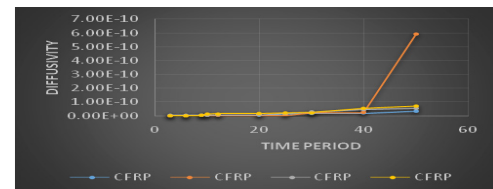


Figure 8. Graph of capacitance results in CFRP.

10. Percentage Weight Gain of Bending Specimen

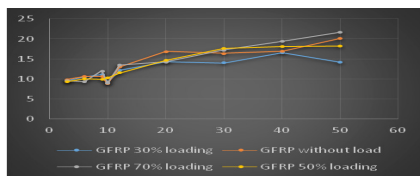
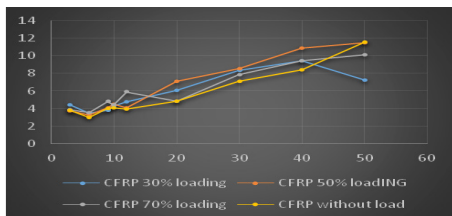
The Percentage weight gain (of moisture) was compared for various loads (shown in Tables 6, 7). It is noted that the percentage weight gain is increasing with respect to time indicating more moisture is absorbed after two months compared to first month in almost all the cases. The moisture absorption of CFRP (Figure 10) specimen is comparatively low as that of GFRP (Figure 9), so more time to degrade. The reason for increasing the weight gain with time is that, the pores of epoxy will loosen due to given hygrothermal load giving way to moisture.

Table 6. Percentage weight gain results of laminated bending composites

Time period	GFRP 30% loading	GFRP without load	GFRP 70% loading	GFRP 50% loading
3	9.58	9.78	9.48	9.25
6	10.51	10.57	9.26	10.00
9	11.13	10.60	11.97	9.88
10	9.14	8.88	8.95	10.29
12	12.17	12.97	13.43	11.50
20	14.37	16.81	14.22	14.69
30	14.01	16.34	17.20	17.65
40	16.58	16.85	19.35	18.11
50	14.15	20.06	21.62	18.22

Table 7. Percentage weight gain in CFRP laminated specimen

Time period	CFRP 30% loading	CFRP 50% loading	CFRP 70% loading	CFRP without load
3	4.39	3.71	3.88	3.80
6	3.48	3.25	3.55	3.00
9	3.80	4.04	4.80	3.98
10	4.26	4.51	4.44	4.10
12	4.75	4.08	5.91	3.94
20	6.05	7.09	4.83	4.83
30	8.34	8.53	7.87	7.07
40	9.45	10.89	9.46	8.39
50	7.22	11.51	10.16	11.58

**Figure 9.** Graph of percentage weight gain in GFRP.**Figure 10.** Graph of percentage weight gain in CFRP.

11. Micro Hardness of Laminates

The micro hardness readings of GFRP and CFRP (Tables 8, 9) laminates specimen decreased when compared to initial readings before hygrothermal treatment due to hardening of epoxy with absorption of water and micro hardness of GFRP (Figure 11) specimen is same at the end of exposure duration, whereas for CFRP (Figure 12) there is no appreciable change after some days.



Table 8. Micro-hardness results in GFRP laminated specimen

Time period	GFRP 30% loading	GFRP without load	GFRP 70% loading	GFRP 50% loading
3	14.75	13.78	15.71	12.85
6	12.81	12.56	13.63	12.79

9	11.95	11.92	12.97	11.60
10	11.12	11.42	12.24	11.10
12	10.42	10.84	11.55	10.88
20	10.34	10.60	10.93	9.74
25	10.16	10.03	10.44	9.70
30	9.96	9.69	9.66	9.58
40	9.66	9.55	9.42	9.01
50	8.22	9.36	8.63	8.91

Table 9. Micro-hardness results in CFRP laminated specimen

Time period	CFRP 30% loading	CFRP 50% loading	CFRP 70% loading	CFRP without load
3	14.53	15.84	12.84	12.79
6	11.70	10.66	11.91	12.22
9	11.35	10.63	11.46	12.07
10	10.66	10.51	11.25	11.23
12	10.59	14.50	11.15	10.94
20	10.44	10.31	10.84	10.37
25	9.41	10.27	9.90	9.96
30	9.39	9.38	9.48	8.75
40	8.94	8.49	9.33	8.69
50	8.40	7.11	9.07	8.60

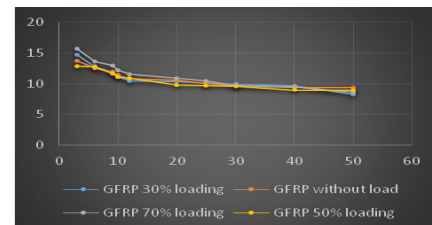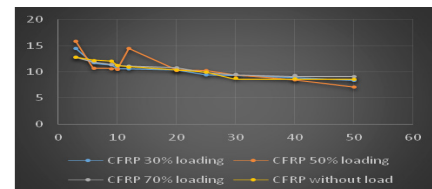**Figure 11.** Graph of micro-hardness in GFRP.**Figure 12.** Graph of micro-hardness in CFRP.

12. % Area Fraction of Bending Laminate

Graphs between %area of fraction and time period is drawn using values shown in Table 10. The GFRP bend-

ing specimen percentage area fraction (Figure 13) for 50%UTL GFRP specimen shows decreasing whereas for 70% UTL CFRP (Figure 14) bending specimen percentage area fraction is almost same after one month and for 70% UTL GFRP specimen decreasing after one month.

Table 10. Percentage area fraction for bending specimen

Time period	%area fraction of fibre (GFRP)	%area fraction of fibre (CFRP)	%area fraction of epoxy (GFRP)	%area fraction of epoxy (CFRP)
Initial	69.2	68.8	30.8	31.2
30% loading (month 1)	67.3	64.1	32.7	35.9
30% loading (month 2)	67.8	57.8	42.2	42.2
50% loading (month 1)	67.3	60.7	32.7	39.3
50% loading (month 2)	60.9	51.3	39.1	48.7
70% loading (month 1)	62.6	33.8	37.4	
70% loading (month 2)	63	34.2	37	

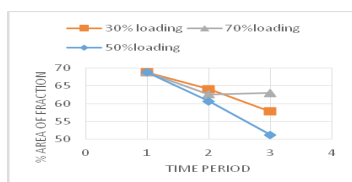


Figure 13. Graph for area of fraction of GFRP.

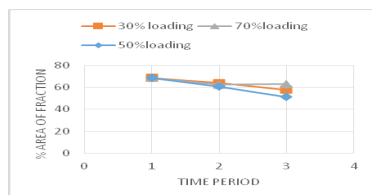


Figure 14. Graph for area of fraction of CFRP.

13. Conclusion

Moisture diffusivity of GFRP specimen is decreasing relatively with time for all specimens whereas for CFRP specimen decrease is almost same for all materials and after one-month moisture diffusivity of CFRP specimen has decreased.

Capacitance of CFRP specimen had not attained saturation as water absorption is slow and the capacitance was increasing with time.

The reduction in strength and damage in fibre is investigated using SEM. It was observed that with increase in % weight gain, micro hardness of specimen decreases. It was also observed that with time % area of fraction of fibre decreases.

14. References

1. Panigrahi SK, Pradhan B. The width delamination damage propagation characteristics in single lap laminated FRP composite joints. *International Journal of Adhesion and Adhesives*. 2009; 29(2):114–24.
2. Saito H, Kimpara I. Damage evolution behaviour of CFRP laminates under post impact fatigue with water absorption environment. *Composites Science and Technology*. 2009; 69(6):847–55.
3. Yashiro S, Ogil K. Fracture behavior in CFRP cross play laminates with initially cut fibres. *Applied and Manufacturing*. 2009 Oct; 77:75–86.
4. Shi X, Hinderliter BR, Croll SG. Environmental and time dependence of moisture transportation in an epoxy coating and its significance for accelerated weathering. Presented at the Coating Tech Conference Indianapolis. 2009; 7(4):419–30.
5. Higgins RMO, McCarthy MA. Comparison of open hole tension characteristics of high strength glass and carbon fiber-Reinforced composite materials. *Composite Science and Technology*. 2008; 68(13):2770–8.
6. Aktas A, Uzun I. Sea water effect on pinned glass fiber composite materials. *Composite Structures*. 2008; 85:59–63.
7. Schambron T, Lowe A, McGregor HV. Effects of environmental ageing on the static and cyclic bending properties of braided carbon fiber /PEEK bone plates. *Composites Part B, Engineering*. 2008; 399(7–8):368–80.
8. Botelho EC, Pardini LC, Rezende MC. Hygrothermal effects on the shear properties of carbon fibre/epoxy composites. *Journal of Materials Science*. 2006; 41:7111–18.
9. Aiello MA, Ombre L. Environmental effects on the mechanical properties of glass-FRP and aramid-FRP rebar. *Mechanics of Composites Material*. 2000; 36:1–30.
10. Purslow D, Potter RT. The effect of environment on the compression strength of notched CFRP a fractographic investigation. *Composites*. 1984 Apr; 15(2):112–20.
11. Sereir Z, Adda-Bedia EA, Tounsi A. Effect of temperature on the hygrothermal behavior of unidirectional laminated plates with asymmetrical environmental conditions. *Composite Structures*. 2006 Mar; 72(3):383–92.

12. Alam MDA, Alriyami K, Jumaat MZ, Muda ZC. Development of high strength natural fibre based composite plates for potential application in retrofitting of RC structure. *Indian Journal of Science and Technology*. 2015 Jul; 8(15):1–7. DOI: 10.17485/ijst/2015/v8i15/70878.
13. Farhana NIE, Majid MSA, Paulraj MP, Ahmadhilmi E. Determination of volume fraction of a glass fibre/ matrix composite plate using vibration analysis. *Indian Journal of Science and Technology*. 2015 Aug; 8(20):1–13. DOI: 10.17485/ijst/2015/v8i20/79114.