

# Recent Advances in Biophysical Stimulation of MSC for Bone Regeneration

Liliana Polo-Corrales<sup>1\*</sup>, Jaime Ramirez-Vick<sup>2</sup> and Jhon Jairo Feria-Diaz<sup>3</sup>

<sup>1</sup>Department of Agroindustrial Engineering, University of Sucre, Cra. 28 #5-267, Puerta Roja, Sincelejo, Colombia; liliana.polo@unisucra.edu.co

<sup>2</sup>Department of Biomedical, Industrial & Human Factors Engineering, Wright State University Dayton, OH. United States of America; jaime.ramirez-vick@wright.edu

<sup>3</sup>Department of Civil Engineering, University of Sucre, Cra. 28 #5-267, Puerta Roja, Sincelejo, Colombia; jhon.feria@unisucra.edu.co

## Abstract

**Objectives:** The purpose of this work was to review the recent advances in biophysical stimulation of MSC for bone regeneration with particular relevance in the tissue engineering field. **Methods/Statistical Analysis:** The review process had three steps: First, by the use of databases available, the principal findings published related to the different types of biophysical stimulation applied to Mesenchymal Stem cells (MSC) for bone tissue regeneration were compiled. Second, the principal characteristics such as historical relevance, conditions of operation, signaling, and principal results were obtained from each study. And third, considering the above characteristics, a description of each study was realized. **Findings:** This review highlighted the following findings: a) The capacity of MSC for differentiating to multiple lineages have attracted attention in regenerative medicine applications; b) Biophysical stimulation is an alternative in order to promote the osteodifferentiation of MSC; c) During the process of application of this type of stimulation, the generation of biochemical signals which is related to the changes in the environment of the cell (i.e., cell attachment, proliferation, and differentiation) are generated; and d) Despite a large number of studies published in this area, these do not explain clearly the mechanisms related to the generation of these signaling produced by the biophysical effects (i.e., mechanical, electrical, and electromagnetic). Furthermore, in this review, a compilation of the last five years was done, which emphasize in the aspect historical, conditions of operation, and biochemical signaling generated of each type of biophysical stimulation of MSC for osteodifferentiation. **Application/Improvements:** Biophysical stimulation causes multiple effects on the cell environment, producing changes in its morphology, proliferation, and differentiation. The above is important in the biophysical stimulation of MSC for bone regeneration.

**Keywords:** Biophysical Stimulation, Bone Regeneration, Osteodifferentiation, Stem Cells, Tissue Engineering

## 1. Introduction

Mesenchymal Stem Cells (MSC) have attracted attention in regenerative medicine applications due to their capacity to differentiate to osteocytes, chondrocytes, adipocytes, hepatocytes, and neurocyte<sup>1</sup>. At present, the mechanisms used in order to direct the differentiation towards specific

lineages are biochemical and biophysical cues<sup>2,3</sup>. Growth factors and small molecules inhibitors are used in the biochemical stimulation of MSC to the bone regeneration. Although this route is effective and easy to apply, nowadays, biophysical cues are being used to stimulate the differentiation of MSC<sup>4</sup>. Many studies have demonstrated that this type of stimulation causes certain effects on stem

\*Author for correspondence


cell attachment, proliferation, and differentiation, but a clear conclusion about the mechanisms of action on cells or the biochemical signal generated by these effects are not well understood<sup>5-7</sup>. For this reason, the changes in cell biochemistry and biology produced by biophysical effects (i.e., interactions with extracellular matrix (ECM) substrate, neighboring cells, external forces, etc.) are an important aspect to highlight. Mechanotransduction allows knowing the cell response towards these physical signals<sup>3,8</sup>. The application of external forces (i.e., mechanical forces) on the cell is recognized by the cellular machinery that detects biochemical signals and changes in the environment. These forces play a critical role in controlling stem cell fate and lineage determination because affecting the structure of ECM. And these effects are associated with mechanically-driven changes in adhesive cues and paracrine signals that modify the cell shape<sup>9</sup>. In the mechanotransduction of bone tissue regeneration, the osteocytes play a role as sensory cells, while osteoblast and osteoclast are generated cells of the process<sup>10</sup>. In this review, recent findings of the different types of biophysical stimulation such as tensile strain, pressure, ultrasound, shear stress, electrical, and electromagnetic

fields that promote the osteodifferentiation of MSC are described and highlighted. (See Figure 1)

## 2. Biophysical Stimulation Types

### 2.1 Tensile Strain

Applied mechanical forces have been shown to induce stem cell differentiation in a lineage-specific manner<sup>11</sup>. In 1976, it was demonstrated that cyclic stretching can stimulate the synthesis of extracellular matrix components. In this experiment, arterial smooth muscle cells subjected to elongation and relaxation increased their rate of collagen, hyaluronate, and chondroitin 6-sulfate synthesis<sup>12</sup>. In others studies, researchers found that tensile strain causes changes in the orientation and morphology of cultured cells from the anterior cruciate ligament in rabbits<sup>13</sup>. Later, the fundamental mechanobiology principles related to the differentiation of MSCs into bone, cartilage, or fibrous tissue were established<sup>14</sup> endochondral ossification, and bone remodeling. It has been shown that all these processes are influenced strongly by the local tissue mechanical loading

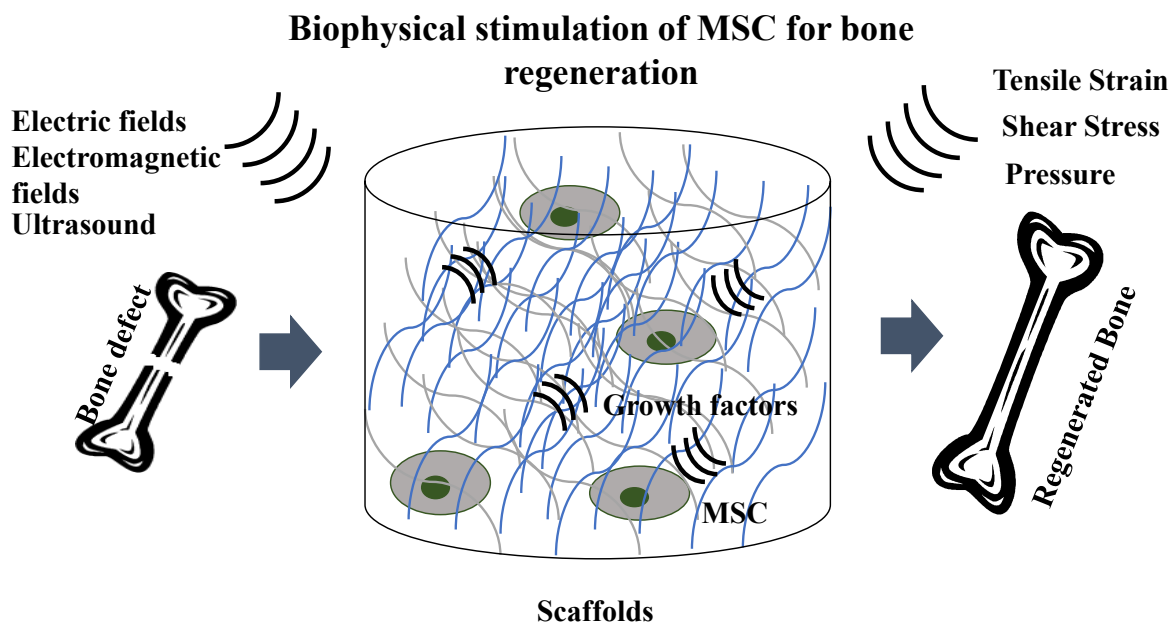

**Figure 1.** Biophysical stimulation of MSC for bone regeneration.

history. This article reviews some of the mechanobiologic principles that are thought to guide the differentiation of mesenchymal tissue into bone, cartilage, or fibrous tissue during the initial phase of regeneration. Cyclic motion and the associated shear stresses cause cell proliferation and the production of a large callus in the early phases of fracture healing. For intermittently imposed loading in the regenerating tissue: These principles predicted various conditions: (1) intramembranous bone formation at low stress and strain; (2) intramembranous ossification at low to moderate tensile strain and hydrostatic tensile stress; (3) chondrogenic differentiation with poor vascularity, in an osteogenic environment and exposed to an hydrostatic compressive stress; (4) fibrous tissue production at high tensile strain; and (5) fibrocartilage formation in the presence of tensile strain and hydrostatic compressive stress. Also, other researchers demonstrated that the intramembranous bone formation is activated by strain and hydrostatic pressure<sup>15,16</sup>. Lately, experimental studies have confirmed MSCs differentiation using mechanical strain<sup>17-19</sup>.

Expression of the FOS family of transcription factors can be induced by mechanical loading, an effect crucial for bone remodeling and osteoblastic differentiation. Findings have demonstrated that cyclic stretch under elongation (2 to 8% elongation at 1Hz for 3 days) induce up-regulation of osteogenic transcription factors (i.e., RUNX2 and FosB) and biomarker (e.g., Type I collagen expression in MSC<sup>20</sup>). Similarly, human mesenchymal stem cells (hMSCs) are highly sensitive to mechanical stretching and this effect can promote the increase of the gene expression levels of osteochondrogenic transcription factors (i.e., FOS, RUNX2, Sox9)<sup>21</sup>. Also, rat bone marrow mesenchymal stem cells (rMSCs) exposed to 1 Hz (2-8% elongation for 15-60 minutes) showed an increase in the proliferation and the expression of the c-Fos gene when stretching above 4%<sup>22</sup>.

Bone morphogenetic proteins (BMPs) play an important role in the development of bone and cartilage<sup>23</sup>. Experimental studies have reported an increase

in BMP-2 expression levels in hMSCs cultured in 3D scaffolds under uniaxial cyclic tensile strain (1 Hz and 0-12% strain) without osteogenic supplements<sup>24</sup>. Results showed that applied uniaxial tensile strains of 10% and 12% resulted in local strains up to 18.3% and 21.8%, respectively<sup>25</sup>. They also demonstrated that cyclic tensile strain can affect the expression of tumor necrosis factor- $\alpha$  (TNF- $\alpha$ ), interleukin-1 $\beta$  (IL-1 $\beta$ ), interleukin-6 (IL-6), and interleukin-8 (IL-8) cytokines, which are involved in bone resorption during osteogenic induction of hMSCs. It was also reported that cyclic tensile strain did not promote the expression of both IL-1 $\beta$  and TNF- $\alpha$ , but induced the expression of IL-8 that could lead to inhibition of bone resorption during osteogenesis<sup>26</sup>. Besides, researchers have studied the cellular mechanism of mechanotransduction in MSCs exposed to cyclic tensile mechanical strain<sup>27</sup>. The results of this study revealed that mechanical strain reduced the rate of MSC proliferation and the strain-induced synthesis of BMP-2 was reduced by inhibitors of the kinases, ERK, p38, and PI3 kinase. In the same direction, it was found that BMP-4 proteins are implicated in the commitment of MSCs toward adipocytes. It has reported that stretching of cells may inhibit BMP-4-induced adipogenesis<sup>28</sup>. In these experiments, the authors applied cyclic equibiaxial elongation (10% strain at 0.25 Hz) for 120 min/day for four days. The results demonstrated that: (1) the cell stretching suppressed BMP-4 induction of C3H10T1/2 MSC adipogenesis, (2) Both BMP-4-triggered SMAD and p38 phosphorylation were not affected by cell stretching, (3) stretching induced significant ERK1/2 phosphorylation, and (4) blocking of ERK deteriorated stretch suppression of BMP-4-induced MSC adipogenesis. The first study on the effect of cyclic tensile strain on osteodifferentiation of human adipose-derived adult stem (hASCs) was reported recently<sup>29</sup>. In this study, cells were subjected to 10% uniaxial cyclic tensile strain (1 Hz for 4 hours per day for up to two weeks) with cycles of 1 s tensile strain followed by a 10 s rest. The results indicated that osteodifferentiation induced by cyclic tensile strain was significantly higher

than unstrained controls. Later, another study<sup>30</sup> indicated that uniaxial cyclic tensile strain can promote osteogenesis in hMSC and hASCs. In this experiment, the cells were seeded in 3D type I collagen constructs and were exposed to 10% cyclic tensile strain. The results indicate that tensile strain induced expression of genes associated with migration, proliferation, musculoskeletal and cardiovascular tissue development. And, an enhanced expression of osteogenic and angiogenic factors was observed.

It has been demonstrated that tensile strain induces differentiation in human dental pulp cells (hDPCs) and human periodontal ligament stem cells (hPDLSCs). Researchers have studied the behavior of hDPCs exposed to cyclic tensile strain (3-15% elongation) at 6 cycles/min for various periods of time. The results of this study showed that the mRNA levels for differentiation markers osteopontin (OPN), bone sialoprotein (BSP), dentin sialophosphoprotein (DSPP), and dentin matrix-protein-1 (DMP-1) were upregulated after 24 h exposure to 12% mechanical stress<sup>31</sup>. However, another group reported that application of extrusive forces had no influence on human pulp tissue<sup>32</sup>. By contrast, it was found that hPDLSCs have a sensitive response to mechanical stimulus. In this study, osteogenic transcription factors were examined under cyclic tensile strain (3,000  $\mu$ strain) with different loading durations<sup>33</sup>. The results showed that mRNA levels and protein expression of osteogenic transcription factors (i.e., *Satb2* and *RUNX2*) increased significantly after 3 hours exposure to tensile strain.

Studies have indicated that physical properties of substrates where MSCs are grown could affect their differentiation. First, it was demonstrated that the application of dynamic stretch can overcome the inhibition of spreading due to the lack of matrix stiffness surrounding the cell<sup>34</sup>. Second, it was reported that the compressive elasticity of a 3D nanofiber matrix stimulates MSCs differentiation to vascular cells. This study was performed at a strain rate of  $0.50\text{mm m}^{-1}\text{ s}^{-1}$  up to a maximum strain of 15 % in the range 2-15 kPa and the results indicated that MSC penetrated into the graft forming a 3D matrix<sup>35</sup>. Third, it

has used a polylactide-co-glycolide (PLGA) nanofiber-based scaffold to evaluate the synergistic effect of both chemical and mechanical stimulation on the fibroblastic differentiation of hMSCs. The results indicated that the application of both stimuli promoted ligament regeneration. However, the authors argue that a good scaffold alignment and optimized mechanical stimulation are sufficient to drive MSC differentiation, without the need for additional chemical stimuli<sup>36,37</sup>.

Tensile strain and chemical stimulation promote osteogenic differentiation of hASCs. Researchers studied the effects of chemical and mechanical stimulation (10% cyclic tensile strain) on the response of hASC<sup>38</sup>. The results showed increased calcium content and upregulation of two crucial factors in bone regeneration: (1) Proinflammatory cytokine regulators *IL1RN* and *SOCS3*; (2) Angiogenic inducers *FGF2*, *MMP2*, and *VEGF A*. Also, other study demonstrated that both chemical and mechanical stimulation can improve osteogenic and chondrogenic differentiation in hASCs<sup>39</sup>. Tensile strain stimulates MSCs differentiation toward cardiac, neural and musculoskeletal tissues. It has reported the generation of tissue-engineered cardiac grafts using MSCs<sup>40</sup>. In this study, effects of strain intensity on cardiac-related gene expressions of rBMSCs were evaluated by cultivating them on flexible membranes subjected to 24 h of uniaxial strain (1 Hz) with different membrane elongations (i.e., 5%, 10%, 15%, and 20%). The results showed high mRNA levels of *GATA-4*, *b-MHC*, *NKx2.5*, and *MEF2c*. Afterwards, they compared the effects of cyclic strain and fluid shear stress (10  $\text{dyn/cm}^2$ ) on the cells, revealing an enhanced cardiomyogenic differentiation under cyclic strain. Similarly, others researchers analyzed the effect of mechanical forces on the development and maintenance of musculoskeletal tissues<sup>41</sup>. They hypothesized that mechanical loading could modulate the transcriptional behavior of MSCs, stimulate the deposition of ECM, and enhance functional properties of constructs. For this purpose, they used a nanostructured poly (e-caprolactone) scaffold and exposed it to cyclic loading at 6% strain with

**Table 1.** Biophysical stimulation of MSC using tensile strain

Tensile strain	Differentiation	Study Type	Comments	Ref
Cyclic stretch of 1 Hz with 2% or 8% elongation	Osteogenesis	In vitro	Cyclic stretch under elongation induced FosB expression and the up-regulation of osteoblast genes.	In <sup>20</sup>
Cyclic uniaxial tensile strain (3000 $\mu$ strain , 1000 cycles at 1 Hz)	Osteogenesis Chondrogenesis	In vitro	Application of mechanical strain promoted early chondrogenic and osteogenic differentiation in vitro.	In <sup>21</sup>
Cyclic uniaxial tensile strain (2000 $\mu$ strains at 0.5 Hz)	Osteogenesis	In vitro	Mechanical loading induced osteogenic differentiation.	In <sup>44</sup>
Cyclic equiaxial stretch ( 2–8% strain at 1 Hz)	-----	In vitro	Equiaxial stretch generated proliferation of rMSCs.	In <sup>22</sup>
Uniaxial cyclic tensile strain (10% or 12% s at 1 Hz)	Osteogenesis	In vitro	Cyclic tensile strain inhibited expression of both IL-1b and TNF-a, but induced the expression of IL-8 which could lead to inhibition of bone resorption during osteogenesis.	In <sup>26</sup>
Uniaxial cyclic stretch ( 0–25%, strain at range of 1–3 Hz )	Smooth muscle cells	In vitro	Cyclic stretch promoted differentiation of hMSCs to smooth muscle cells without addition of growth factors.	In <sup>223</sup>
Uniaxial cyclic tensile strain (10% at 1 Hz )	Osteogenesis	In vitro	Cyclic tensile strain accelerated hASC osteodifferentiation and increased calcium content.	In <sup>29</sup>
Cyclic tensile strain (2.5% at 0.17 Hz )	Osteogenesis	In vitro	Cyclic tensile strain modulated osteogenic differentiation of MSCs.	In <sup>27</sup>

Table 2 Continued

Cyclic tensile strain ( 3-15% elongation at 6 cycles/min )	Osteogenesis	In vitro	Cyclic tensile strain induced odontoblastic differentiation via Nrf2-regulated HO-1 expression.	In <a href="#">31</a>
Cyclic tensile strain ( 6% at 1 Hz)	Fibro-chondrogenesis	In vitro	Cyclic loading stimulated the expression of matrix and matrix-associated genes.	In <a href="#">41</a>
Equibiaxial and uniaxial cyclic tensile stretch ( 10% at 1Hz )	-----	In vitro	Equibiaxial stretch promoted spreading of rounded cells on soft substrates.	In <a href="#">34</a>
Uniaxial cyclic tensile strain (10% at 1 Hz)	Osteogenesis Angiogenesis	In vitro	Cyclic tensile strain enhanced promoted angiogenesis and osteogenic differentiation of hMSC from osteoporotic donors.	In <a href="#">30</a>
Uniaxial Cyclic tensile strain ( 3,000 $\mu$ strain at 0.5 Hz)	Osteogenesis	In vitro	Cyclic tensile strain stimulated osteogenic differentiation of human periodontal ligament stem cells.	In <a href="#">33</a>
Cyclic uniaxial tensile strain ( 5-20%, elongation at 0.5- 2 Hz)	Chondrogenesis	In vitro	Cyclic strain is a better stimulant of rBMSC differentiation toward the cardiomyocyte lineage than shear stress.	In <a href="#">40</a>
Uniaxial cyclic tensile strain (3% and 1 Hz)	-----	In vitro	The genetic expression of MSCs under cyclic tensile strain is different in both 2D and 3D system.	In <a href="#">43</a>
Cyclic tensile stretch (10% strain, 0.25 Hz.	Osteogenesis	In vitro	Cyclic tensile strain suppressed adipogenic differentiation of MSCs during BMP4 treatment.	In <a href="#">28</a>
Cyclic tensile loading ( 0.5, 2 and 3.5%) at ( 0.5, 1 and 1.5 Hz)	Neurogenesis Osteogenesis	In vitro	Cyclic tensile loading at low amplitude and frequency promoted neurogenic differentiation in MSCs.	In <a href="#">42</a>



Table 1 Continued

Cyclic tensile stretch (0 to 4000 $\mu$ strains at 0 and 2Hz )	Chondrogenesis	In vitro	Cyclic tensile strain induced PTHrP expression in postnatal growth plate prehypertrophic and hypertrophic chondrocytes.	In <sup>224</sup>
Cyclic tensile strain (1% at 1 Hz)	Fibroblast cells	In vitro	Mechanical and chemical stimulation promoted fibroblastic induction of hMSCs in nanofiber scaffold.	In <sup>225</sup>

a frequency of 1 Hz for 3 hours, stimulating the expression of type I collagen, Type II collagen, fibronectin, and lysyl oxidase. Also, it was demonstrated that different cyclic tensile loadings produce different microfilament rearrangement and promote neuron-like differentiation of hMSCs<sup>42</sup>.

Experimental studies have confirmed that gene expression of MSCs under cyclic tensile strain is different in 2D and 3D culture systems<sup>43</sup>. In this work, gene expression of hMSCs was studied under cyclic tensile strain (3% and 1 Hz) in monolayer culture or encapsulated in a peptide hydrogel. In 2D culture, CCNL2, BAHCC1, and WDR61 were significantly downregulated. However, after 24 h strain, BAHCC1 was significantly upregulated. In contrast, in 3D culture, the BAHCC1 gene was not expressed. The authors argued that the mechanical cues affect cells differently in 3D cultures. Finally, other important advances in this field have been the study of bone regeneration during distraction osteogenesis, which involves cellular and complex molecular processes<sup>44</sup>. Important results have indicated that when rBMSCs were exposed to cyclic uniaxial tensile strain (0.5 Hz, 2000  $\mu$ strains) for 40 minutes, the upregulation in the expression of osteogenic markers (i.e., ALP, Cbfa1/RUNX2, and Ets-1) was generated. Table 1 shows some recent advances in biophysical stimulation of MSC generated by tensile strain.

## 2.2 Hydrostatic Pressure and Compression

Mechanical stimulation is considered as the fourth strategy in bone tissue engineering along with the use of cells, scaffolds and growth factors<sup>45</sup>. It activates MSCs function in different manners<sup>46</sup> causing changes in morphology, proliferation, and differentiation<sup>47</sup>. In the last fifteen years, researchers have confirmed that the fluid mechanical forces activate signaling transduction in osteoblasts<sup>48</sup>. Researchers found a correlation between characteristic parameters of cyclic pressure and cellular functions in osteoblasts and osteoclasts<sup>49-51</sup>. A first study demonstrated the dependence of osteoblast proliferation on the duration of the applied cyclic pressure stimulus. They used osteoblasts, fibroblasts, and endothelial cells, which were exposed to a range of pressure of 10-40 kPa at 1 or 0.25 Hz frequency for one hour each day for five days. The results showed that osteoblast proliferation decreased at 1Hz frequency while decreasing mRNA expression of ALP after five days. Also, under this condition fibroblasts showed an increase in cell proliferation, while endothelial cells were not affected. A second study showed evidence of a correlation between mechanical loadings on osteoclast formation using the same range of pressure for 1 Hz for the same time frame to stimulate progenitor bone marrow cells. These results display a decrease of osteoclast cell formation and lower bone resorption under cyclic pres-

sure, which was supported by down-regulation of mRNA expression for IL-1- $\alpha$ , IL-1 $\beta$ , and TNF- $\alpha$ . In a third study, they used the same conditions of cyclic pressure for one hour daily for different time periods up to 19 days to validate the effects on certain functions of osteoblasts relevant to osteogenesis. The results showed that osteocalcin (OCN) mRNA expression did not increase while Type I collagen mRNA expression increased only when cells were exposed for 19 consecutive days. In addition, they observed that the amount of acid-soluble collagen and calcium content increased after 19 days of exposure.

Investigations have confirmed that mechanical loading plays an important role in the differentiation, maturation, and senescence of hMSCs<sup>52</sup>. An important finding in this field has reported the study of the gene expression patterns of stimulated cells under both dynamic tension and dynamic compression at 0.1 Hz frequency<sup>53</sup>. The results indicated that dynamic tension up-regulated genes associated with bone formation and inhibited chondrogenesis, while dynamic compression regulated chondrocyte proliferation and upregulated genes associated with chondrogenesis. Similarly, other studies have demonstrated that chondrogenic differentiation of hMSCs can be modulated by frequency and amplitude of dynamic compression and shear stress<sup>54-57</sup>. Additionally, it has shown evidence of chondrogenesis in hMSCs using fibrin scaffolds under cyclic compression<sup>58</sup>. Also, it has compared the effect of dynamic hydraulic compression (DHC) stimulation on hASCs and hMSCs<sup>59</sup>. The results of this study indicated that DHC (1 psi at 1Hz frequency) increased osteogenic gene expression in both types of cells with hMSCs being more susceptible. Besides, it has investigated the role of estrogen and its receptors in the mechanobiological effects in bone mesenchymal stem cells (BMSCs)<sup>60</sup>. The results of this study demonstrated that both mechanical compression and estrogens stimulated the proliferation and differentiation of BMSCs via F-actin. The application of pressure on the system caused alterations in the cytoskeleton via the orientation and alignment of fibers, forming thick fibrous

structures. First, it was reported that static (23 kPa) and dynamic (10–36 kPa and at 0.25 Hz frequency) hydraulic pressure stimulated osteodifferentiation of MSCs<sup>61,62</sup>. In this study was found that both types of pressure promoted the expression osteogenesis-related factors of MSCs and also induced osteoclastogenesis. Second, it has investigated the effects of the low-intensity intermittent negative pressure effects on the proliferation and differentiation of hMSCs<sup>63</sup>. The results of this study indicated that under these conditions, proliferation was inhibited while inducing osteogenic differentiation. Researchers has demonstrated that hydrostatic pressure (HP) affects cell response during co-culture<sup>64-67</sup>. In a first study, it was monitored the degree of differentiation of MSCs into nucleus pulpous (NP)-like cells via mechanical stimulation. It was used a 3D co-culture system with 0.2 MPa of applied pressure with intervals of 2 min for pressurizing and 15 minutes for resting. The results showed that MSCs did not differentiate under mechanical stimulation when cultured alone, but tended to differentiate immediately when NP cells were nearby. In a second study, it was monitored the migration of MSCs with or without neighboring endothelial cell under the effects of intermittent HP (100 and 200 mm Hg, 5 minutes pressure and 10 min rest). The results displayed that HP only stimulated the migration of MSCs when endothelial cells were not nearby. In a third study, chondrogenic differentiation of MSCs in 3D co-culture under mechanical stimulation was analyzed. In this study, MSCs were co-cultured with primary chondrocytes into separate alginate beads divided by a membrane. Afterwards, they were stimulated with different conditions of intermittent hydrostatic pressure (IHP). The results indicated that the stimulation using higher magnitudes IHP promoted the proliferation and differentiation of co-cultured MSCs even without biochemical agents. Finally, in a recent study, it was found that both dynamic compression and co-culture with nucleus pulpous cells stimulated the proliferation and chondrogenic differentiation of hASCs.



Hydrostatic pressure can play a key role in regulating the chondrogenic differentiation of MSCs. It has found the following findings:

- The long-term exposure to HP stimulates the formation of cartilaginous tissue, but this effect varies depending on the donor<sup>68</sup>.
- Chondrogenic differentiation of hASCs in collagen scaffolds under cyclic HP stimulation<sup>69</sup>.
- Chondrogenic differentiation of hASCs using intermittent HP and biochemical stimulation<sup>70</sup>. The interaction of both biochemical and biophysical stimulation might regulate chondrogenesis of joint tissue-derived stem cells<sup>71</sup>. In this study, the cells were stimulated with different concentrations of TGF- $\beta$ 3 and 10 MPa of cyclic HP. The results showed that physical stimulation with low concentrations of TGF- $\beta$ 3 acts synergistically to increase chondrogenesis.
- A comparative study with hASCs and hMSCs to examine cell viability in 3D agarose constructs without soluble growth factors under the application of cyclic HP<sup>72</sup>. In this study, the cells were exposed to 7.5 MPa at a frequency of 1 Hz for up to 21 days. The results showed that at day 7 both cell types initiated chondrogenic differentiation, but at day 14 a decrease in cell metabolic activity was presented by both cells indicating that perhaps the agarose hydrogel was not an appropriate 3D structure for chondrogenic differentiation of hASCs in long-term culture.
- Dynamic HP acts to maintain a chondrogenic phenotype in cartilaginous grafts engineered<sup>73</sup>. In this study, it was monitored the phenotypic stability of chondrogenic differentiation of multipotent stromal cells, and infrapatellar fat pad derived multipotent stromal cells (FPSCs) seeded on agarose hydrogels subject to 10 MPa of cyclic

HP (1Hz). The results displayed an increase in the accumulation of reduced sulfated glycosaminoglycan content in both cell types, an increase of the collagen content in multipotent stromal cells but not in FPSCs, a decrease in calcium deposition within multipotent stromal cells seeded constructs maintained in chondrogenic medium, and no evidence of calcium deposition on FPSCs.

- A study about of the biochemical properties and gene expression of MSCs on hybrid scaffold exposed to cyclic HP (5 MPa, 0.5 Hz)<sup>74</sup>. Researchers demonstrated that hydrostatic pressure increased type II collagen mRNA levels but no aggrecan and Sox9 levels. These results differed from others researchers who reported an increase in mRNA expression of aggrecan, type II collagen, and Sox9 in hBMSCs under HP. In addition to HP stimulation, also is crucial a favorable environment for the MSCs differentiation<sup>75</sup>.
- Chondrogenic differentiation of MSCs is regulated by matrix stiffness, integrin binding and cytoskeletal organization, necessary for mechanotransduction of hydrostatic pressure<sup>76</sup>.
- Cyclical uniaxial compressive stress affects the morphology, cytoskeleton rearrangement, and the production of proteoglycans by the expression of osteogenic markers (i.e., RUNX2 and ALP activity) via phosphorylation of myosin light chain II (MLCII)<sup>77</sup>.

The use of three-dimensional (3D) bone constructs and hydrostatic pressure stimulation have proven to be a good option to promote osteogenic differentiation of MSCs. Researchers demonstrated that the combined effects of biochemical and biophysical stimulation encourage osteogenic differentiation of hMSCs in scaffolds<sup>78</sup>. In this study, hMSCs were cultured on collagen

**Table 2.** Biophysical stimulation of MSC using hydrostatic pressure and compression

Conditions	Differentiation	Study Type	Comments	Ref
Cyclic Pressure (10 - 40) kPa at 0.25 or 1.0 Hz.	-----	In vitro	Duration applied cyclic pressure affected osteoblast proliferation.	In <sup>49</sup>
Cyclic Pressure (10 - 40) kPa at 0.25 or 1.0 Hz.	-----	In vitro	Duration applied cyclic pressure stimulus affected osteoclast formation and bone resorption activity.	In <sup>50</sup>
Cyclic Pressure (10 - 40) kPa at 0.25 or 1.0 Hz.	-----	In vitro	Osteoblast functions related to new bone formation were promoted by cyclic pressure stimulus.	In <sup>51</sup>
Compression or tension under displacement controlled sinusoidal dynamic loading at 0.1 Hz	Osteogenesis Chondrogenesis	In vitro	Dynamic tension up-regulated genes associated with bone formation and inhibited chondrogenesis and dynamic compression regulated chondrocyte proliferation and upregulated genes associated with chondrogenesis.	In <sup>53</sup>
Intermittent Hydrostatic Pressure at 0.2 MPa	Chondrogenesis	In vitro	Hydrostatic pressure stimulated chondrogenic differentiation of MSCs co-culturing with NP cells.	In <sup>64</sup>
Intermittent Hydrostatic Pressure(100 and 200 mm Hg)	-----	In vitro	Hydrostatic pressure stimulated the migration of MSCs in the absence of endothelial cells neighboring.	In <sup>65</sup>
Static Pressure (23 kPa) or Dynamic Pressure (10–36 kPa at 0.25 Hz)	Osteogenesis	In vitro	Static and dynamic pressure promoted the expression osteogenesis-related factors of MSCs during the initial process of osteoblastic differentiation.	In <sup>61</sup>
Static Pressure (23 kPa) or Dynamic Pressure (10–36 kPa at 0.25 Hz)	Osteogenesis	In vitro	Static and dynamic pressure promoted osteoclastogenesis with the up-regulation of RANK/OPG ratio during the initial process of osteoblastic differentiation	In <sup>62</sup>
Cyclic Hydrostatic Pressure (300 – 375 kPa at 0.5 Hz).	Osteogenesis	In vitro	Biophysical and Biochemical stimulation promoted osteogenic differentiation of hMSCs.	In <sup>78</sup>

Table 2 Continued

Pressure of -50 kPa at frequency of 2/d,	Osteogenesis	In vitro	Low-intensity intermittent negative pressure inhibited the proliferation of cells but induced osteogenic differentiation.	In <sup>66</sup>
Cyclic Hydrostatic Pressure ( 10 MPa of at 1 Hz)	Chondrogenesis	In vitro	Application of long-term hydrostatic pressure stimulated the formation of cartilaginous tissues but the effects change depending donor.	In <sup>68</sup>
Cyclic Hydrostatic Pressure (10 MPa at 1Hz)	Chondrogenesis	In vitro	The application of hydrostatic pressure with low concentrations of TGF- $\beta$ 3 acted synergistically to increase chondrogenesis in MSCs.	In <sup>71</sup>

and/or chondroitin sulfate coated polycaprolactone-co-lactide substrates under cyclic HP stimulation (300 kPa and 375 kPa) at 0.5 Hz. The results showed that osteogenic differentiation of hMSCs was promoted by both chondroitin sulfate and cyclic HP. At the same time, it was dependent on stimulation time. In another study also it was demonstrated that both hydroxyapatite scaffolds and cyclic hydrostatic pressure enhance the cellular viability, stimulate osteogenic differentiation, and period of maturation, but at the same time, decrease proliferation and self-renewal of MSCs. Similarly, it has reported chondrogenic differentiation of MSCs in hydrogels (i.e., agarose or fibrin) with the presence of growth factors under HP stimulation<sup>79</sup>. The results of this study indicated that agarose hydrogels better-supported chondrogenesis than fibrin hydrogels, and the application of HP increased sulfated glycosaminoglycan's synthesis in fibrin hydrogels, but not in agarose hydrogels. Also, HP did not stimulate the synthesis of collagen in either fibrin or agarose predicting that both HP stimulation and scaffold material are essential factors in the cartilage regeneration and maintenance of a chondrogenic phenotype. Recent studies have demonstrated that MSC seeded on substrates based on polycaprolactone (PCL) exposed to the combina-

tion of intermittent hydrostatic pressure (270 kPa, 1Hz for 1minute daily for 21 days) and osteogenic medium of substrates of PCL nanofibers, stimulated the production of osteogenic markers such as Collagen type I, ALP activity and RUNX2<sup>80</sup>. Table 2 shows recent findings that highlight osteodifferentiation of MSC using hydrostatic pressure and compression.

### 2.3 Ultrasound

Ultrasound is an oscillating sound pressure wave that produces local changes of the medium's density and pressure, and exerts both thermal and nonthermal effects on liquids and in soft tissues<sup>81-83</sup>. Low-intensity ultrasound is considered a nonthermal technique that decreases tissue heating and cavitation phenomena. It also involves acoustic streaming, acoustic cavitation, and acoustic microstreaming, which increase blood flow, stimulate the cell activity, disturb the membrane permeability, and activates the second messengers's system<sup>81,83-85</sup>. The effects produced by the nonthermal technique are divide into two categories(put reference 86): inertial cavitation(higher acoustic pressures) and....is in the range between 6 and 8 W/m<sup>2</sup>. These biophysical effects on the cellular plasma membrane and cytoskeleton stimulate the production of

growth factors, osteogenic differentiation, and ECM production<sup>87</sup>. Also, ultrasound transfers mechanical energy into tissues increasing the mechanical strength of the callus formed after bone healing, nitric oxide production, activation of transcription factors (e.g., hypoxia-inducible factor-1 $\alpha$ ). These effects induce the expression of vascular endothelial growth factor (VEGF) in osteoblasts and reduce the time to bone union<sup>88,89</sup>. Similarly, mathematical models have predicted that the cellular response to ultrasound depends on both frequency and specific cell properties<sup>90</sup>. However, the mechanisms by which ultrasound can interact with cells and/or their microenvironments during fracture healing are not clear. In the early 1900s, Low Intensity Pulsed Ultrasonic (LIPUS), a longitudinal wave with regions of rarefactions and compressions began to be used to treat fractures with 1 MHz sine waves repeating at 1 kHz, with an average intensity of 30 mW/cm<sup>2</sup> for 200  $\mu$ s giving a 20% duty cycle, which were applied for 20 minutes per day<sup>82</sup>. Later, a commercial LIPUS device for fracture healing and treatment of nonunion was designated by Exogen (Smith & nephew, Inc., London, UK) and was approved by the FDA in 1994. Nowadays, this technique is being used as a mechanism to promote osteogenic and chondrogenic differentiation of MSCs<sup>91</sup>. This technique has been used in wide range of studies including complex tibial fractures<sup>92-94</sup>, anterior cruciate ligaments<sup>95</sup>, osteoporotic fractures<sup>96</sup>, and osteonecrosis of femoral heads<sup>97</sup>, bilateral midshaft femur fractures<sup>98</sup>, osteoradionecrosis<sup>83</sup>, reconstruction of patella-patellar tendons<sup>99</sup>, dental tissue repair<sup>87</sup>, and tibial distraction osteogenesis<sup>100</sup>. Nonetheless, studies have demonstrated that therapeutic ultrasound has no significant effect in severe articular cartilage injuries<sup>89</sup>.

In the last years, researchers have reported chondrogenic differentiation of mesenchymal stem cells (MSCs) by low-intensity ultrasound (LIUS) stimulation. Some important studies are described to following.

- Chondrogenic differentiation of MSCs without the presence of transforming growth factor-beta (TGF- $\beta$ ), a critical factor for initiation of chondrogenic differentiation<sup>101</sup>. In this study, the effect

of LIUS (1MHz and 200 mW/cm<sup>2</sup>) on rMSCs in a 3D alginate culture increased the expression of chondrogenic markers (i.e., type II collagen, aggrecan, and Sox-9). Later, it was found that LIUS stimulation inhibited apoptosis, improved cell viability and, increased chondrogenic differentiation of MSCs<sup>102</sup>. In this study, hMSCs were cultured in 3D alginate scaffolds in the presence of growth factors (i.e., TGF- $\beta$ 1) with/without LIUS (1MHz and mW/cm<sup>2</sup>). The results displayed that the LIUS-stimulated cells showed balanced expression of apoptosis-related genes (i.e., p53 and bax) and antiapoptotic proteins (i.e., bcl-2, and PCNA), and enhanced the expression of chondrogenic markers (i.e., Sox-9, aggrecan, and type II collagen).

- LIUS stimulation increased the collagen and glycosaminoglycan content in vivo without the presence of chondrogenic growth factors<sup>103</sup>. In this study, MSCs cultured in polyglycolic acid (PGA) scaffolds were implanted in the back of nude mice and stimulated with ultrasound (0.8 MHz and 200 mW/cm<sup>2</sup>). In contrast, in another study, it was reported enhanced chondrogenic differentiation of hMSCs in pellets cultured under both TGF- $\beta$ 1 treatment and LIUS stimulation<sup>104</sup>.
- LIUS stimulation (1 MHz and 100 mW/cm<sup>2</sup>) promotes cell adhesion and improves the colony-forming capacity of MSCs during the early cell attachment stage of primary cultures<sup>105</sup>. In this study, the stimulated cells and the control presented the following characteristics: (1) no changes in size distribution of colonies; (2) no changes in the overall expression patterns of cell surface antigens (i.e., CD29, CD90, and CD106, and CD45); and (3) same differentiation capacity for three different cell lineages (i.e., osteogenic, adipogenic, and chondrogenic). Also, LIUS stimulation could induce expression of cell adhesion molecules (i.e., integrin  $\alpha$ 5, integrin  $\beta$ 1,

**Table 3.** Biophysical stimulation of MSC using ultrasound

Conditions	Differentiation	Study Type	Results	Ref
1MHz and 200 mW/cm <sup>2</sup> (LIUS)	Chondrogenesis	In vitro	LIUS stimulated chondrogenic differentiation in MSCs cultured on alginate beads without TGF- $\beta$ treatment.	In <sup>101</sup>
0.8 MHz and 200 mW/cm <sup>2</sup> (LIUS)	Chondrogenesis	In vivo	LIUS had great potential in stimulating the chondrogenic differentiation of MSCs in vivo without using chondrogenic growth factors.	In <sup>103</sup>
1MHz and 200 mW/cm <sup>2</sup> (LIUS)	Chondrogenesis	In vitro	LIUS inhibited apoptosis of MSCs and enhanced their viability during chondrogenic differentiation.	In <sup>102</sup>
1MHz and 100 mW/cm <sup>2</sup> (LIUS)	Osteogenesis Adipogenesis Chondrogenesis	In vitro	LIUS activated cell adhesion and increased the colony-forming ability of MSCs during the early stage of primary culture, without affecting their phenotypes and multipotency.	In <sup>105</sup>
1MHz and 200 mW/cm <sup>2</sup> (LIUS)	Chondrogenesis	In vitro	LIUS enhanced chondrogenesis of the MSCs cultured in fibrin-Hyaluronic Acid hydrogels.	In <sup>226</sup>
2, 15 and 30 mW/cm <sup>2</sup> (LIPUS)	Osteogenesis	In vitro	LIPUS intensities lower than those currently used clinically showed a positive effect on osteogenic differentiation of MSCs.	In <sup>106</sup>
1.5 MHz, 30 mW/cm <sup>2</sup> (LIPUS)	Osteogenesis	In vivo	LIPUS induced the homing of circulating osteogenic progenitor to the fracture site for possible contribution to new bone formation.	In <sup>107</sup>
(1, 100, and 1000 Hz) LIPUS	Osteogenesis	In vitro	LIPUS accelerated osteogenic differentiation of hASCs based on amount of calcium accretion normalized by total DNA.	In <sup>91</sup>
LIPUS / microgravity	Osteogenesis	In vitro	LIPUS treated SMG cultures had higher collagen content in ECM and more matrix calcification	In <sup>108</sup>

Table 3 Continued

1 MHz, 200 mW/ cm <sup>2</sup> (LIPUS)	Osteogenesis	In vitro	The synergistic effect of LIPUS and RGD promoted proliferation and differentiation of MSCs.	In <a href="#">109</a>
Ultrasonic Bioreactor (5.0 MHz, 2.5 Vpp)	Chondrogenesis	In vitro	Ultrasound and TGF- $\beta$ treatment promoted chondrogenesis of MSCs seeded on polymeric scaffolds that limit cell-to-cell contact.	In <a href="#">110</a>
1 MHz, 50 mW/ cm <sup>2</sup> , duty cycles at 20 and 50 % (LIPUS)	Osteogenesis	In vitro	LIPUS enhanced cell viability and osteogenic differentiation.	In <a href="#">111</a>
1.5 MHz, 30, 60, and 90 mW/cm <sup>2</sup> (LIPUS)	Osteogenesis	In vitro	LIPUS stimulation facilitated osteogenic differentiation associated with activation of integrin $\beta$ 1- and upregulation of RUNX2 expression.	In <a href="#">112</a>

paxillin, and fibronectin) and enhance focal adhesion via phosphorylation of focal adhesion kinase (FAK).

In the last years, various studies have been reported related to osteogenic and chondrogenic differentiation of MSCs using LIPUS stimulation. It has found the following studies:

- The effects on rBMSC at early, middle, and late stages of osteogenic differentiation caused by LIPUS with lower intensities used clinically (2, 15, and 30 mW/cm<sup>2</sup>)<sup>[106](#)</sup>. The results showed modulation of the ERK1/2 and p38 pathways, with the highest increase of mineralization at 2 mW/cm<sup>2</sup>.
- New bone formation in femoral fractures in mouse using LIPUS stimulation<sup>[107](#)</sup>. In this study, it was reported accelerated fracture healing of transverse femoral fractures in mouse by LIPUS

stimulation. Also, it was found that both local and circulating osteogenic progenitors promoted new bone formation.

- The effects produced by LIPUS stimulation on hASCs and hMSCs at different pulse repetition frequencies (PRF) (i.e. 1, 100, and 1000 Hz)<sup>[91](#)</sup>. The results showed osteogenic differentiation in both cell types at different PRF, obtaining the highest amount of calcium per DNA at 1 kHz.
- The effects of LIPUS stimulation on cell proliferation and osteogenic differentiation of hASCs under simulated microgravity<sup>[108](#)</sup>. The results showed that LIPUS stimulation increased ALP activity and the expression of osteogenic genes (i.e., ALP, OSX, RANKL, and RUNX2), and reduce the expression of OPG. It was also observed under these conditions the restoration of ALP activity, increased OSX, RUNX2, and RANKL expression,



and an increase in the production of collagen and calcium.

- The synergistic effect of LIPUS stimulation and RGD-grafted oxidized sodium alginate/N-succinyl chitosan (RGD-OSA/NSC) hydrogels, which enhanced cell proliferation and osteogenic differentiation of hMSCs<sup>109</sup>. In this study, it was suggested that cell differentiation resulted from an increase in cell membrane permeability, signal transduction, and improvement of the interaction between cytokines and RGD.
- Cell proliferation and chondrogenic differentiation of hMSCs in 3D scaffolds by ultrasonic stimulation (5MHz and 2.5 Vpp) and the presence of TGF- $\beta$ <sup>3</sup><sup>110</sup>.

The osteogenic differentiation of dental stem cells by LIPUS stimulation has also been shown. Investigations in this field have reported that a change in duty cycle can influence migration and osteogenic differentiation of human alveolar bone-derived mesenchymal stem cells (hABMSCs)<sup>111</sup>. Similarly, it has demonstrated that LIPUS can promote osteogenic differentiation of hPDLs<sup>112</sup>. Finally, it has reported osteodifferentiation by acoustic stimulation of MSC in absence of fetal bovine serum<sup>113</sup>. Table 3 shows some important studies that demonstrate osteogenic and chondrogenic differentiation of MSC using ultrasound.

## 2.4 Shear Stress

Applied external forces can affect the shape and fate of stem cells<sup>114</sup>. In the last few years, theoretical studies have reported that fluid shear regulates MSCs differentiation by affecting the transport of bioactive factors, cell deformation and cytoskeletal strain<sup>115</sup>. A mathematical model based on the theory that octahedral shear strain and interstitial fluid flow was designed to estimate how mechanical stimulation affects tissue differentiation towards cartilage<sup>116</sup>. Data from the healing of a transverse osteotomy

was found consistent and supported by this model, demonstrating that MSC differentiation is influenced by the distribution of these two components<sup>115</sup>. Other researchers published results showing MSC differentiation under specific tensile strains and fluid perfusion flows. They determined that low shear stress induces the production and release of a number of paracrine factors which inhibit MSCs apoptosis and contribute to quiescence<sup>117,118</sup>.

ERK 1/2 and p38 activity are members of the mitogen-activated protein kinase (MAPK) family which serve as focal points in response to a variety of extracellular stimuli such as environmental stresses and inflammatory cytokines<sup>119,120</sup>. In this topic some researchers have found the following:

- hBMSCs are influenced by fluid shear stress, inducing cellular responses related to bone cell differentiation<sup>121</sup>. In this study, bone marrow stromal cells were exposed to a fluid shear of 12 dynes/cm<sup>2</sup> for 30 and 90 min, showing an important increase in ALP expression regulated by p38 activity and a decrease of type I collagen expression downregulated by ERK1/2. Nonetheless, fluid shear exposure did not affect Cbfa1/RUNX2 expression, suggesting that it could not be related to ALP activity<sup>122</sup>.
- Furthermore, connexin 43 (CX43) expressions was confirmed indicating cell-to-cell communication in hBMSCs through gap junctions<sup>6</sup>.

Fluid shear stress activates ERK1/2 signaling<sup>123</sup>. In this study, intermittent loads (mean value: 4.2 dyn/cm<sup>2</sup> for 1h at intervals of 0.34 dyn/cm<sup>2</sup> for 11 h) of fluid shear stress were applied to hBMSCs increasing the expression of osteogenic genes (i.e., RUNX2, ALP, Collagen and OCN) and ALP activity via two novel signaling pathways. In addition, other researchers have presented evidence suggesting that shear stress alone, without induction factors, can stimulate hMSCs towards the osteoblastic pheno-

type<sup>124</sup>. In this study hMSCs were exposed to 4, 15 and 22 dyn/cm<sup>2</sup> of shear stress for 24 h showing an increase in the expression of the osteogenic markers ALP, BMP-2 and Osteopontin (OPN).

MSCs gene expression can be affected by the shear stress magnitude and exposure time, with the latter being the most influential at an early stage of osteogenesis<sup>125</sup>. In a study, cells were exposed to 0.2 or 1 dyn/cm<sup>2</sup> for 30 or 60 min resulting in upregulation of RUNX2, Type I collagen, and Sox9 markers with no change in the expression of aggrecan, PPAR $\gamma$ , and Osterix (OSX). However, others researchers confirmed that the magnitude of shear stress is crucial for the differentiation of MSCs<sup>126</sup>. They found that the expression of myocardin, myosin heavy chain, and SM-22a was higher when exposed to 10 dyn/cm<sup>2</sup> compared with 2.5 dyn/cm<sup>2</sup>. Also, it has indicated that the variation in shear stress levels affects gene expression on hMSCs<sup>127</sup>. In this study, applied shear stresses of 0.015, 0.030, 0.045 and 0.060 Pa caused upregulation of type I collagen and OPN expression. Lately, DNA microarray and quantitative real-time reverse transcription-PCR analysis showed up-regulation of MAP3K8 and interleukin-1 beta expression in MSCs exposed to different magnitudes and duration of flow-induced shear stress<sup>128</sup>, while uniaxial tensile strain and magnetic forces did not induce any effect<sup>129</sup>.

Fluid shear stress can regulate MSCs differentiation into cardiomyogenesis. Researchers have reported an increase in cardiomyogenic differentiation in rBM-SCs exposed to laminar shear stress (i.e., 5, 10, 15 and 20 dyn/cm<sup>2</sup> for 24 hours)<sup>130</sup>. The results of this study showed various issues: (1) An increase in the expression of GATA4, b-MHC, NKx2.5 and MEF2c at < 10 dyn/cm<sup>2</sup> and a decrease in their expression at 15 dyn/cm<sup>2</sup>, (2) An increase of the expression of cTnT, CX43, desmin and a-sarcomeric actinin, (3) Enhanced activity of the L-type calcium channel; and (4) an increase in the level of Atrial Natriuretic Peptide (ANP) protein. Similarly, it has been demonstrated that the combination of shear stress and compression has a higher influence on chondrogenic differentiation of MSCs than either stimulus alone<sup>131</sup>. For instance, a pin-on-ball bioreactor system was used on

porous polyurethane scaffolds under the following conditions: (a) Compression: 1 Hz, 0.4 mm (amplitude); (b) Shears: 1 Hz,  $\pm 25\%$  (amplitude); (c) Both compression and shear. A mechanical load was applied during 1 h per day for 5 consecutive days per week over 3 weeks. The results demonstrated that this combination causes progression of MSCs towards a chondrogenic phenotype. Also, it has demonstrated an increase in chondrogenesis of hBMSCs by exposure to cyclic axial compression and surface shear stress<sup>132</sup>.

Fluid shear stress may induce MSC differentiation into endothelial cells. Some important findings are described to following.

- Differentiation of MSC into endothelial cells<sup>133</sup>. In this study, hMSCs differentiated into endothelial cells creating a capillary network in 3D culture under both, in vitro and in vivo conditions.
- Differentiation of MSCs into endothelial cells using a 3D scaffold and a pulsatile flow bioreactor<sup>134</sup>. In this study, the scaffold was subjected to 1 to 15 dyne/cm<sup>2</sup> for two days and at 15 dyne/cm<sup>2</sup> for two days. Under these conditions, the expression levels of VE-cadherin, PECAM-1, and CD34 were increased while smooth muscle markers were downregulated. On the other hand, some researchers have exposed hASCs to 10 dyn/cm<sup>2</sup> for 24, 48, and 96 h showing an increase in VEGF expression, due to an increase in nitric oxide production, with no expression of endothelial cell markers (i.e., CD31, vWF, Flk-1)<sup>135</sup>.

Important findings have compared osteogenic differentiation of MSCs under different fluid shear conditions. Some important findings are showed to following.

- Osteogenic commitment produced by cytoskeletal remodeling is correlated with vibration but not fluid shear<sup>136</sup>. To demonstrate this, adipose-derived hMSCs were subjected to vibration frequencies and acceleration magnitudes that

**Table 4.** Biophysical stimulation of MSC using shear stress

Conditions	Differentiation	Study Type	Comments	Ref
12 dyn/cm <sup>2</sup>	Osteogenesis	In vitro	ERK1/2 and p38 signaling are both required for hBMSCs to respond shear stress and regulate osteoblastic phenotype.	In <sup>121</sup>
4, 15 and 22 dyn/cm <sup>2</sup>	Osteogenesis	In vitro	Shear stress stimulated osteogenic differentiation without chemical induction.	In <sup>124</sup>
4.2 dyn/cm <sup>2</sup>	Osteogenesis	In vitro	Fluid shear stress activates ERK1/2 signal and induces osteogenic differentiation of hMSCs.	In <sup>123</sup>
0.2 and 1 dyn/cm <sup>2</sup>	Chondrogenesis	In vitro	Duration of exposure to mechanical stress provides a more powerful stimulus for differentiation of multipotent cells than stress magnitude.	In <sup>125</sup>
2.5 and 10 dyn/cm <sup>2</sup> .	Smooth muscle cells	In vitro	High shear stress may disturb the differentiation of MSCs into Endothelial Cells in the presence of endothelial growth medium, but may promote differentiation to Smooth Muscle Cells.	In <sup>126</sup>
5,10,15 and 20 dyn/cm <sup>2</sup>	Cardyomiogenesis	In vitro	Fluid shear stress induced cardyomiogenic differentiation of rBMSCs.	In <sup>130</sup>
10 dyn/cm <sup>2</sup>	Endothelial cells	In vitro	Fluid shear stress did not induce the expression of endothelial cell markers in hASCs.	In <sup>135</sup>
2.3 dyn/cm <sup>2</sup> and 4.3 dyn/cm <sup>2</sup> at 0.015, 0.044, and 0.074 Hz.	Osteogenesis	In vitro	Pulsatile flow enhanced osteoblastic differentiation of osteoprogenitor cells.	In <sup>138</sup>

Table 4 Continued

0.34 and 4.2 dyn/cm <sup>2</sup>	Osteogenesis	In vitro	Intermittent fluid shear stress promoted enhanced osteogenic differentiation compared to continuous fluid shear stress and up-regulated the activity of ERK1/2 and FAK.	In <a href="#">137</a>
1 and 15 dyn/cm <sup>2</sup>	Endothelial cells	In vitro	Shear stress upregulated the expression of endothelial cell-related markers and downregulated smooth muscle-related markers in canine MSCs.	In <a href="#">134</a>
Parallel flow (1.0x10 <sup>-4</sup> dyn/ cm <sup>2</sup> ) Transverse flow (5.5x10 <sup>-3</sup> dyn/ cm <sup>2</sup> )	Osteogenesis	In vitro	Parallel flow allowed the effective retention of de novo ECM proteins and growth factors and promoted osteogenic differentiation of hMSCs.	In <a href="#">139</a>
0.15, 0.30, 0.45 and 0.60 dyn/cm <sup>2</sup>	Osteogenesis	In vitro	Shear stress associated with vascular flow may have the potential to significantly direct non-adherent stem cell expression towards osteogenic phenotypic expression.	In <a href="#">127</a>
0.41 – 0.51 dyn/cm <sup>2</sup>	Osteogenesis	In vitro	Osteogenic differentiation by Rocker culture method.	In <a href="#">142</a>
0.01 - 0.0205 dyn/cm <sup>2</sup>	Osteogenesis	In vitro	Osteogenic differentiation by Rocker culture method.	In <a href="#">141</a>
0.231 and 1.089dyn/ cm <sup>2</sup>	Osteogenesis	In vitro	YAP expression in MSCs and chondrocytes is regulated by fluid shear stress.	In <a href="#">140</a>
0.5 – 3 dyn/cm <sup>2</sup> .	Chondrogenesis	In vitro	Chondrogenic differentiation of MSCs was observed in the presence of chondrogenic supplements under both static and laminar flow cultures.	In <a href="#">227</a>

induced fluid shear stress ranging from 0.04 Pa to 5 Pa and vibrations were applied using frequencies of both 100 and 30 Hz during 30 min/day.

- Intermittent fluid shear stress promotes enhanced osteogenic differentiation compared to continuous fluid shear stress<sup>137</sup>. This effect increases the expression levels of osteogenic markers (i.e., ALP, RUNX2, OCN, and Type I collagen) and promoted the activity of ERK1/2 and FAK.
- Osteoblastic gene expression when osteoprogenitor cells were cultured in a perfusion bioreactor<sup>138</sup>. In this study, BMSCs were exposed to steady (2.3 dyn/cm<sup>2</sup>) and pulsatile flow (range: 2.3 - 4.3 dyn/cm<sup>2</sup>, frequencies: 0.015 - 0.074 Hz) for 24 h and maintained in static osteogenic medium for an additional 13 days. They found a significant increase in gene expression of type 1 collagen, osteopontin (OPN), osteocalcin (OCN), and bone sialoprotein (BSP) under both conditions and for TGF- $\beta$  and BMP-2, BMP-7 under pulsatile flow alone.
- Studies performed in a bioreactor with two perfusion flow conditions (a) parallel (shear stress:  $\sim 1 \times 10^{-5}$  Pa) and transverse (shear stress:  $\sim 5.5 \times 10^{-4}$  Pa) showed osteogenic differentiation of MSC<sup>139</sup>. In this experiment, MSCs were exposed to these conditions using normal growth media during the first 7 days, then to osteogenic induction media for an additional 7 days. Results revealed that cell proliferation was maintained during both the pre-induction and osteogenic induction stage under parallel flow conditions. In contrast, under transverse flow system, a similar cell proliferation rate was seen during the pre-induction stage, which was reduced after osteogenic induction due to the convective removal of proteins and growth factors.
- Studies performed in a microfluidic perfusion system allowed to study the influence of fluid shear

stress in the regulation of yes-associated protein (YAP) expression in MSCs and chondrocytes<sup>140</sup>. The results indicated increased YAP expression, osteogenic differentiation favored over adipogenesis for MSCs, and initial dedifferentiation for chondrocytes.

- Some researchers studied the behavior of different types of cell (i.e., human alveolar bone-derived MSCs, human dermal fibroblast and embryonic stem cell-derived mesenchymal progenitor cell lines) under oscillatory fluid shear stress (Rocker culture method)<sup>141</sup>. The results showed an increase in ALP activity and calcium deposition when osteogenesis was induced in the system.
- Finally, the effect of osteogenic media and fluid shear stresses on human progenitor dermal fibroblasts (HDFs) and an embryonic stem cell-derived mesenchymal progenitor cell line (i.e., hES-MP) also has been studied<sup>142</sup>. Results of this study indicated that both biochemical and biophysical stimulation promoted osteogenic differentiation on both cell types.

Lately, the effects of fluid shear stimulation on human periodontal ligament cells<sup>143</sup> and human Alveolar Bone-Derived Mesenchymal Stem Cells<sup>144</sup> have been reported. It has demonstrated that the cells under shear stress experiment a rearrange in the orientation of the cells inducing osteogenic differentiation. Similarly, oscillatory fluid flow promotes the upregulation of osteogenic gene expression, production of collagen, and mineral deposition<sup>145</sup>. Besides, the combination of fluid shear stimulation and the addition of growth factors into the system of cell culture of MSC stimulate the osteodifferentiation of human mesenchymal progenitor cells (hMPCs). Equally, an increase in perfusion velocity applied to MSC, increase the mineralized matrix growth<sup>146</sup>. Some important findings of biophysical stimulation of MSC using shear stress are shown in Table 4.

## 2.5 Electric Fields

Electrical stimulation in bone healing has been used since the 19<sup>th</sup> century to treat tibial non-unions by the use of shock of electrical fluids<sup>147,148</sup> and galvanic current<sup>149</sup>. In 1955, some researchers reported that bone healing could be induced by electrical energy<sup>150-153</sup>. In 1957, Fukada and Yasuda measured the piezoelectric properties of bone and their use in fracture healing<sup>154</sup>. Also, Bassett and coworkers proposed that electrical potentials could influence the activity of osseous cells. They indicated that the activation of the piezoelectric properties of the collagen matrix, the electro-kinetic effects, and the polarity of applied current stimulate the formation of new bone in electronegative regions, and induce resorption in the electropositive regions<sup>155-157</sup>. In addition, many publications have confirmed this phenomenon<sup>158-162</sup>. Similarly, clinical case reports confirmed the use of electrical stimulation for bone healing<sup>163,164</sup>. All these studies used technologies that can be classified into three types of electrical stimulation, which have been approved by FDA for clinical use: direct current (DC), and inductive coupling (IC) such as pulsed electromagnetic fields (PEMF) and combined magnetic fields (CMF), and capacitive coupling (CC)<sup>156</sup>.

In the last year, many researchers have reported that electrical stimulation promotes MSC differentiation. Researchers have compared the aspect such as cell adhesion and orientation in 3D scaffolds in bone marrow-derived mesenchymal stem cells (BMMSCs) and fibroblast under electrical stimuli<sup>165</sup>. The results of this study showed that MSCs exhibited more 3D adhesion and also a minimal alteration in cell reorientation compared to fibroblasts that presented perpendicular reorientation. Also, in this study, they incubated the cells with integrin antibodies under the same conditions and found a lack of response, which indicated that integrin-mediated mechanism is likely to regulate 3D cell morphology and orientation. Also, studies have reported the behavior of cell migration of MSCs exposed to electric fields. Other study indicated that MSCs exposed to direct currents

of 10 to 600 mV/mm had strong migration towards the anode with double the speed of the control<sup>166</sup>. In addition, it was demonstrated that the cell migration in a physiological electric field is cell passage-dependent since migration is reduced at higher passages, and the exposition to electric fields do not affect the osteogenic potential of the cells. Another important finding was the development of a 3D tissue model of osteoblast wound healing to examine the effects of electrophysiological modulation on bone regeneration<sup>167</sup>. Others researchers have monitored the differentiation profile and stress response of human bone marrow-derived mesenchymal stem cells (hMSCs) exposed to electric fields<sup>168</sup>. In this study, cells were exposed to 20 mV/cm (60 kHz) for 40 minutes daily and the results revealed overexpression of the early bone marker (ALP), mid marker (type 1 collagen), and upregulation of heat shock proteins (hsp27, hsp70) which are stress response and cellular metabolism markers, respectively. However, the authors suggested that further studies are necessary to establish possible relationships between applied electric field, stress response markers, and osteogenic markers on osteodifferentiation.

Researchers demonstrated for the first time that cultured human adipose tissue-derived stem cells (hASCs) can be modulated by DC electric fields<sup>169</sup>. They stimulated the cells with DC electric fields of 6 V/cm for 2-4 hours and observed: (1) Elongation and perpendicularly alignment to the applied electric field, (2) Disassembly of gap junctions, (3) Upregulation of certain genes (i.e., CX43, thrombomodulin (ThB), vascular endothelial growth factor (VEGF), and fibroblast growth factor (FGF); and (4) Lack of upregulation of osteopontin (OPN) and peroxisome proliferator-activated receptor gamma (PPAR $\gamma$ ). Also, researchers have evaluated for first time the effects of sinusoidal AC electric fields on hASCs, and demonstrated that short-term (i.e., 1, 10, 100, or 1000 V/cm at 1 Hz for 5 min) and long-term (i.e., 1, 3, and 5 V/cm at 1 Hz for 4-h/day) electric field exposure increases intracellular calcium signaling and calcium deposition in osteogenic differentiation medium, respectively<sup>170</sup>. Likewise, the first



**Table 5.** Biophysical stimulation of MSC using electric fields

Conditions	Differentiation	Study Type	Comments	Ref
4, 7, and 10 V/cm	-----	In vitro	Electrical stimulus regulated mesenchymal stem cell adhesion and orientation in 3D collagen scaffold.	In <a href="#">165</a>
6 V/cm	Fibroblastic and vasculogenic differentiation	In vitro	Direct current electric fields modulated morphological and phenotypic characteristics of hASCs.	In <a href="#">169</a>
Wave electric stimulus: DC, CC, PEMF and DW.	Osteogenesis	In vitro	DW or CC electrical stimulus enhanced rate of bone healing at the fracture site compared to DC and PEMF.	In <a href="#">171</a>
Short-term (1, 10, 100, or 1000 V/cm at 1 Hz) Long-term (1, 3, and 5 V/cm at 1 Hz )	Osteogenesis	In vitro	Sinusoidal AC electric fields on hASCs increased intracellular calcium signaling and calcium deposition under osteogenic differentiation medium respectively.	In <a href="#">170</a>
10 – 600 mV/mm	Osteogenesis	In vitro	Electric Fields directed migration of MSCs mainly to the anode.	In <a href="#">166</a>
200 mV/cm at 60 kHz	Osteogenesis	In vitro	Electrical stimulation promoted osteogenic differentiation and activated osteogenic pathways.	In <a href="#">168</a>
250 mV	Neurogenesis	In vitro	Electrical stimulation and exogenous Nurr1 gene expression together may induce nerve regeneration using stem cells.	In <a href="#">172</a>
Rectangular pulses (7 ms, 3.6 mV/cm, 10 Hz)	Osteogenesis	In vitro	Combined treatment of biochemical and physical microenvironments increased osteogenic differentiation of MSCs.	In <a href="#">179</a>
0.15 V/cm for at 1 Hz	Cardiomyogenesis	In vitro	Carbon nanotubes based polylactic acid scaffolds and electrical stimuli promoted the upregulation of cardiac markers.	In <a href="#">173</a>

Table 5 Continued

500 V/m and 5 ms pulse width at 1 Hz.	Cardiomyogenesis	In vitro	Carbon nanotubes based poly-ε-caprolactone scaffolds and electrical stimuli promoted cardiomyogenic differentiation.	In <sup>174</sup>
Rectangular pulses (2 ms, 100 mV , 10 Hz)	Neurogenesis	In vitro/ in vivo	Electrically induced neural differentiation of mouse BMSCs contributed to the regeneration and recovery of motor function after transplantation into TBI model mice.	In <sup>176</sup>
Rectangular pulses( 2 ms, 40 μA , 2 Hz)	Cardiogenesis	In vitro	Electrical stimulation promoted cardiogenesis in MSC and cardiac myocytes coculture monolayer.	In <sup>175</sup>
Alternating electric current (10 or 40 mA, 10-Hz )	Osteogenesis	in vitro	Alternating electric current promoted the differentiation of adult human MSCs toward the osteogenic pathway.	In <sup>180</sup>

study that compared the effects of various electric stimulation (ES) waveforms on MSCs cellular activities including cytotoxicity, proliferation, cell-kinetics, and apoptosis in vitro were reported in 2011<sup>171</sup>. In this study, they analyzed the effects of direct current (DC), capacitive coupling (CC), pulsed electromagnetic field (PEMF), and degenerate wave (DW) on BMMSCs differentiation. The results indicated that DW and CC conditions had a greater influence on invasion and cell proliferation compared to the other types of electric stimulation being relevant to bone regeneration.

Studies have presented evidence suggesting that MSCs exposed to electrical stimulation may differentiate into nerve, cardiac, and neuronal cells. Some important results are described below.

- Simultaneous electrical stimulation and exogenous Nurr1 gene expression may induce nerve

regeneration using stem cells<sup>172</sup>. In this study, cells were exposed to electrical stimulation (250 mV for 1000 s) and exogenous Nurr1 gene delivery. The results indicated that cells transfected with exogenous Nurr1 genes plus electrical stimulation showed the greatest level of neurite outgrowth compared to one only stimulus.

- CNT based polylactic acid scaffolds and electrical stimuli promoted the upregulation of cardiac markers<sup>173</sup>.
- CNT-poly (ε-caprolactone) (PCL) substrates promoted the differentiation of hMSCs into cardiomyocytes<sup>174</sup>.
- Design of an electric system to stimulate canine MSCs into cardiomyocytes<sup>175</sup>.

- Electrical stimulation can induce differentiation of mouse BMSCs into neural cells<sup>176</sup>. In this study, the cells were transplanted into traumatic brain injury (TBI) model mice. The results indicated that these cells promoted neurogenesis and the recovery of motor function in this animal model.

The combination of electrical stimulation and biochemical agents induces osteogenic differentiation of MSCs<sup>177,178</sup>. Researchers have studied the synergistic effects of biochemical microenvironments (artificial matrix extracellular and osteogenic supplements), and physical microenvironments (electrical stimulation) with respect to osteogenic differentiation of hMSCs<sup>179</sup>. In this study, it was found that the cell exposed to both conditions exhibited an increase in the expression of ALP activity and osteogenic markers (i.e., RUNX2, ALP, and OPN). Also, it has reported MSCs osteodifferentiation by combining alternating electric current and growth factors (i.e., BMPs)<sup>180</sup>. In this study, MSCs were cultured within type I collagen hydrogels, and exposed to either 10 or 40 mA (10 Hz) for 6 h per day which promoted osteogenic differentiation evidenced by the expression of both early (RUNX2 and OSX) and late (OSP and OCN) osteogenic genes.

Of late, the substrates with conductive characteristic are being used to induce osteogenesis. It has found that the use of both electric current and conductive carbon nanotubes (CNTs) in cell-substrate enhance the osteoblastic activity of MSC<sup>181</sup>. Also, the use of electrically conductive scaffold that allows the ion fluxes further migration of MSC into the inner region of the scaffold and enhance the osteogenic differentiation<sup>181,182</sup>. Finally, an important finding highlights that the effects produced by electrical stimulation on the osteogenic differentiation of MSC in early stages are stronger<sup>181</sup>. Table 5 shows some recent advances in biophysical stimulation of MSC generated by electric fields.

## 2.6 Electromagnetic Fields

Electromagnetic fields (EMFs) play a role in the regeneration of several human tissues. In 1974, Bassett and coworkers were pioneers in the therapeutic use of extremely low frequency (ELF) pulsed electromagnetic fields (PEMFs) to accelerate the fracture repair and to treat congenital and acquired pseudarthroses and non-unions<sup>183,184</sup>. In 1979, PEMFs therapy was approved by the FDA<sup>188</sup> allowing clinical trials and production of commercial devices to promote bone fracture healing<sup>186</sup>. Since then, different effects of PEMF stimulation on differentiation and proliferation of some osteogenic cell lines in vitro have been published in the literature<sup>187-190</sup>. Researchers have indicated the forced-vibration of all the free ions on the surface of a cell's plasma membrane, changes in voltage, and conductivities are a possible mechanism of the application of electromagnetic fields to regulate cell process<sup>191-193</sup>. Since then, many investigations have focused on the use of this therapy to accelerate the cell proliferation and osteogenic differentiation of MSC.

In the last years, many studies have demonstrated the effectiveness of PEMFs in the regulation in osteogenesis in MSCs. It has reported the eddy currents induced by ELF-EMF exposure (60Hz, 3 mT) significantly stimulate collagen synthesis in osteoblast-like MC3T3-E1 by p38 MAPK pathways<sup>194</sup>. Additionally, it has indicated that both PEMFs and inductive stimulus like bone morphogenetic protein 2 (BMP-2) induce osteogenic differentiation and impact cells at specific states of commitment to an osteoblast phenotype and maturation period<sup>195</sup>. In this study, it was applied PEMF for 8 hours per day, which consisted of 4.5 ms bursts of 20 pulses repeating at 15 Hz with an increase in field strength from 0 to 16 gauss in 200 ms and decay back to 0 in 25 ms during each pulse. Results showed that under both conditions, ALP activity and osteocalcin expression increased and improved the effect of BMP-2 on PGE2, latent and active TGF- $\beta$ 1, and osteoprotegerin. Furthermore, it has studied the influence of PEMFs (300 ms quasi-rectangular pulses with a

**Table 6.** Biophysical stimulation of MSC using Electromagnetic Field

Conditions	Differentiation	Study Type	Comments	Ref
Helmholtz coil (Biomet, Parsippany, NJ) [Bassett, 1974]	Osteogenesis	In vitro	PEMF enhanced osteogenesis of hMSCs in the presence of an inductive stimulus like BMP-2.	In <sup>195</sup>
Quasi-rectangular pulses ( 7.5 Hz and 0.13 mT)	Osteogenesis	In vitro	PEMF stimulation may play a modulating role in hMSC osteogenesis	In <sup>196</sup>
ELF magnetic field (15 Hz, 1mT)	Osteogenesis	In vitro	Oligo osteogenesis microarray analysis.	In <sup>201</sup>
Helmholtz coil (Biomet, Parsippany, NJ) [Bassett, 1974]	Osteogenesis Adipogenesis Neurogenesis	In vitro	PEMF might change the expression of ion channel and induce membrane hyperpolarization of BMMSCs resulting in the alteration of cell cycle progression and the presence of osteoblasts at different stages of osteogenesis.	In <sup>202</sup>
Helmholtz coil (Biomet, Parsippany, NJ) [Bassett, 1974]	Osteogenesis	In vitro	PEMF increased cell proliferation in human BMMSCs during osteogenesis in the presence of osteogenic medium.	In <sup>203</sup>
ELF magnetic field (50 Hz , 0-20 mT)	Osteogenesis	In vitro	Extremely Low Frequency (ELF) magnetic fieldsinhibited the growth and metabolism of hMSC, but not affected osteogenic differentiation in hMSCs.	In <sup>204</sup>
ELF magnetic field (15 Hz, 1mT)	Osteogenesis Adipogenesis	In vitro	Extremely Low Frequency (ELF) magnetic fieldspromoted osteoblastic differentiation instead of adipogenesis in rMSCs.	In <sup>197</sup>
15 Hz, 1 Gauss with 5-millisecond bursts with 5-microsecond pulses.(Orthopulse® II, IMD)	Osteogenesis	In vitro	PEMF stimulated osteogenesis in BMSCs.	In <sup>208</sup>

Table 6 Continued

ELF magnetic field (15 Hz, 5 mT)	Chondrogenesis	In vitro	Extremely low frequency (ELF) magnetic fields stimulated chondrogenic differentiation of hMSCs.	In <a href="#">209</a>
ELF magnetic field (50 Hz, 0.5 mT)	Osteogenesis	In vitro/ In vivo	Extremely low frequency (ELF) magnetic fields promoted the proliferation, osteogenic differentiation in vitro (Bone Marrow Stromal cells) and in vivo (mice femur) experiments.	In <a href="#">198</a>
PEMF (2 mT, 75 Hz and pulse of 1.3 msec)	Osteogenesis	In vitro	PEMF enhanced the commitment of BM-MSCs to osteoblasts more efficiently in comparison with ASCs	In <a href="#">199</a>
ELF- PEMF (6 gauss at 10, 30, and 100 Hz)	Osteogenesis	In vitro	ELF- PEMF increased cell proliferation and osteogenic response on hAMSCs.	In <a href="#">200</a>
ELF-Magnetic fields (50 Hz, 1 mT)	Neurogenesis	In vitro	PEMF induced neural differentiation in BMMSCs without any chemicals or differentiation factors.	In <a href="#">211</a>
ELF-Magnetic fields (50 Hz or 100 Hz, 1 mT)	Neurogenesis	In vitro	ELF-magnetic fields accelerated neural differentiation of BMMSCs via ROS-induced EGFR activation and, subsequently, Akt and CREB phosphorylation.	In <a href="#">212</a>
PEMF (1 Gauss at 15 Hz, 5 ms bursts with a pulse of 1 ms)	Osteogenesis	In vitro	PEMF and DHEA (prohormone) promoted the viability, proliferation, and osteogenic differentiation of MSCs.	In <a href="#">213</a>
PEMF (1.5 mT at 75 Hz with a pulse of 1.3 ms )	Chondrogenesis	In vitro	PEMF might inhibit the catabolic activity of IL-1 $\beta$ during cartilage-regenerating surgical interventions	In <a href="#">210</a>

Table 6 Continued

PEMF frequencies (1.1 mT at 5, 25, 50, 75, 100, and 150 Hz)	Osteogenesis	In vitro	Different pulsed electromagnetic field frequencies had different effects on induction of bone formation and an optimal frequency for osteogenic differentiation of hMSCs was 50 Hz.	In <sup>219</sup>
High PEMF( 50 – 100 $\mu$ V/cm at 27.1 MHz, pulsed frequency of 1000Hz, and pulse lasting 100 ms)	Osteogenesis	In vitro	PEMF stimulation without the use of chemical increased the expression of osteogenic markers in osteoprogenitor cells.	In <sup>214</sup>
ELF-Magnetic fields(1 mT at 30/45 Hz, and 1 mT at 7.5 Hz,)	Osteogenesis	In vitro	The effects of the electromagnetic fields on osteogenic differentiation differed depending on the electromagnetic field conditions.	In <sup>215</sup>
ELF-Magnetic fields(1 mT at 50 Hz)	Neurogenesis	In vitro	ELF- magnetic fields and magnetic nanoparticles promoted neural differentiation of MSCs.	In <sup>228</sup>

repetition rate of 7.5 Hz and 0.13 mT) on the proliferation and osteogenic differentiation of hMSCs *in vitro*<sup>196</sup>. The results of this study demonstrated a high proliferation rate, and osteogenic differentiation with the time that was supported by the gene expression of RUNX2 at early and mid-stages of culture and calcium accumulation at the highest levels of the culture period. Similarly, it has demonstrated that EMFs (15 Hz, 1mT) play a vital role in balancing the osteoblastic and adipogenic differentiation of MSCs, inhibiting adipogenesis, and stimulating osteoblastic differentiation<sup>197</sup>. Also, the effects of low-intensity EMFs (50 Hz, 0.5 mT) on cell proliferation, differentiation, and cycle in mouse bone marrow stromal cells (BMSCs) *in vitro* and *in vivo* has been investigated<sup>198</sup>. Their results showed that EMFs induce ALP secretion, and not only increase collagen I gene expression but also

DNA synthesis and replication. Others researchers have reported that PEMFs ( $2 \pm 0.2$  mT,  $75 \pm 2$  Hz, and pulses of 1.3 msec) enhanced the commitment of BM-MSCs to osteoblasts more efficiently in comparison with ASCs<sup>199</sup>. And, cell proliferation and osteogenic response of human alveolar bone-derived mesenchymal stem cells (hABMSCs) exposed to EMFs<sup>200</sup>.

Mounting evidence suggests that the application of PEMFs affect the cell proliferation and osteogenic differentiation, through modulation of growth factors, intracellular signaling molecules and, pro-or post-differentiation genes<sup>201</sup>. Researchers used an oligo-osteogenesis microarray to detect the effect of PEMF (15 Hz, 1mT, 8 hr/day for 2 days) on gene expression during the process of MSC cell differentiation. Their results showed that the mRNA levels of BMP1, BMP7 were significantly



higher than EGF and EGFR. Studies have demonstrated that PEMFs induce membrane hyperpolarization in MSCs resulting in the alteration of cell cycle progression<sup>202</sup> and the presence of osteoblasts at different stages of osteogenesis<sup>203</sup>. In the first study, the results indicated that the alteration of cell cycle progression promoted cell proliferation during the exponential growth phase and multi-lineage differentiation potential of bone marrow mesenchymal stem cells (BMMSCs). In the second study, the results suggested that PEMF altered early osteogenesis-related gene expression, up-regulated the expression of *cbfa1/Runx2* at early stages of the culture process, and increased mineralization at early and middle stages of BMMSC osteogenic differentiation. Finally, it has demonstrated that EMFs could inhibit the growth and metabolism of hMSCs, but have no significant effect on their differentiation<sup>204</sup>. These results showed that the effect of EMFs on hMSCs resulted in high proliferative activity, no changes in the morphology, cell viability, higher extracellular  $\text{Na}^+$  ions concentration, higher osmolality, and calcium deposition.

It has been demonstrated that the activation of ERK1/2, via phosphorylation regulates differentiation of MSCs towards the osteoblast lineage<sup>205</sup>, which might be activated by mechanical stimuli (i.e., fluid flow or strain)<sup>206</sup>. Similarly, researchers have provided evidence of the activation of MAPK and ERK in HL-60 human leukemia cells, MCF-7 human breast cancer cells, and rat fibroblast cells exposed to a 60 Hz, 1 G EMF<sup>207</sup>. However, another study reported that EMF stimulated osteogenic differentiation without activating ERK phosphorylation, significantly increasing the ALP activity or the matrix mineralization timing<sup>208</sup>. Therefore, EMF may induce differentiation at the expense of proliferation. EMF has also been able to stimulate MSCs toward a chondrogenic and neural phenotype. Important findings have demonstrated that ELF-EMF (15 Hz, 5 mT) can stimulate chondrogenic differentiation of hMSCs in vitro and affect them at higher passages more distinctively<sup>209</sup>. Similarly, it has reported that PEMFs may inhibit the catabolic activity of IL-1b,

during cartilage-regenerating surgical interventions<sup>210</sup>. In addition, it has found that ELF-EMF (50 Hz, 1 mT) can induce neural differentiation in BM-MSCs without any chemicals or differentiation factors, and accelerate neural differentiation of BM-MSCs *via* ROS-induced EGFR activation<sup>211,212</sup>.

Researchers demonstrated that the application both PEMF and DHEA (prohormone) promotes the viability, proliferation, and osteogenic differentiation of MSCs<sup>213</sup>. They suggested a therapy based PEMF early during fracture healing followed by administration of DHEA with an osteogenic differentiating effect. Moreover, it was demonstrated an increase in the osteogenic response of osteoprogenitor cells (C3H10T1/2) to high-frequency PEMF stimulation without the use of osteogenic media<sup>214</sup>. The results display an improvement in ALP activity and matrix mineralization, cellular proliferation, stimulation of the late stage of osteogenic differentiation, moderate expression of p38 $\alpha$  mRNA, and an increase of mRNA expression of numerous BMPs. The effects produced by EMFs on osteogenic differentiation in MSCs can vary depending on their frequency, waveforms, and intensity. Researchers reported the effects of positive (30/45 Hz, 1 mT) and negative (7.5 Hz, 1-2 mT) EMFs on osteogenic differentiation of hASCs<sup>215</sup>. The results showed a higher expression level of osteogenic markers at positive EMFs and lower at negative EMFs, while both still supporting osteogenic differentiation. The authors argue that this behavior might be related to motion and higher efflux of ions ( $\text{Ca}^+$ ) through the membrane allowing osteoblastic function and viability at specific frequencies<sup>216-218</sup>. Similarly, it has reported, that different PEMF frequencies produce distinct effects on hMSCs differentiation<sup>219</sup>. In this study were used different PEMF frequencies (5, 25, 50, 75, 100, and 150 Hz) each with a field intensity of 1.1 mT, for 30 minutes per day for 21 days. The results indicated that at 50-Hz PEMFs the levels of ALP and Osteocalcin are increased. Also, it was demonstrated that in a range from 5 to 50 Hz, as the frequency increased the inductive effect on bone differentiation also increased.

However, the inductive effect decreased with the increase of the frequency from 50 to 150 Hz. It was also demonstrated that waveforms of EMF are crucial parameters to induce the response of osteoblasts<sup>220</sup> and different electric field intensities could regulate the formation of osteoclast-like cells<sup>221</sup>. Lately, an important study in this field has highlighted that PEMFs promote osteodifferentiation of MSC only when they are precommitment<sup>222</sup>. Table 6 shows recent findings that highlight osteogenic differentiation of MSC using electromagnetic fields.

### 3. Conclusion

After the use of cell culture, scaffolds, and growth factors, biophysical stimulation has been used as a tool in bone regeneration. This type of stimulation causes effects on the cell morphology, proliferation, and differentiation. The different types of biophysical stimulation cause multiple effects on the cell environment and some of these effects are as follows:

- Expression of transcription factors take place during osteogenic differentiation i.e., FOS family and Bone Morphogenetic Proteins (BMPs).
- Osteodifferentiation in different types of MSC.
- Cardiac, neural, chondrogenic, and musculoskeletal differentiation of MSC.
- Difference in genetic expression of MSC with the culture system (2D and 3D).
- The combination of biophysical stimulation, the use of scaffolds, and the addition of growth factors into the system of cell culture of MSC, has resulted in an excellent option to stimulate the osteodifferentiation of MSC.
- Better conditions to promote the osteodifferentiation are reached when the stimulation is applied in early stages.

- Nowadays, the mechanisms that explain the signaling generated by biophysical stimulation (i.e., mechanical, electrical and electromagnetic) are not entirely clear. Therefore, it is necessary to conduct more research on the effects produced by this type of modulation, which will serve in the application of clinical therapies.

### 4. References

1. Ullah I, Subbarao RB, Rho GJ. Human mesenchymal stem cells - current trends and future prospective Bioscience Reports. Bioscience Reports. 2015; 35(191):1-18. Crossref. PMID:25797907 PMCID:PMC4413017.
2. Ding S, Kingshott P, Thissen H, Pera M, Wang P. Modulation of human mesenchymal and pluripotent stem cell behavior using biophysical and biochemical cues: A review. Biotechnology Bioengineering. 2017; 114(2):260-80. Crossref. PMID:27531179.
3. Yim EKF, Sheetz MP. Force-dependent cell signaling in stem cell differentiation. Stem Cell Research & Therapy. 2012; 3(41):1-12. Crossref.
4. Ramirez-Vick JE. Biophysical Stimulation for Bone Regeneration. JSM Biotechnology and Biomedical Engineering. 2013; 1(2):1-1014.
5. Li B, Moshfegh C, Lin Z, Albuschies J, Vogel V. Mesenchymal stem cells exploit extracellular matrix as mechanotransducer. Scientific Reports. 2013; 3(2425):1-8. Crossref.
6. Guilak F, Cohen D, Estes B. Control of stem cell fate by physical interactions with the extracellular matrix. Cell Stem Cell. 2009; 5(1):17-26. Crossref. PMID:19570510 PMCID:PMC2768283.
7. Nava MM, Raimondi MT, Pietrabissa R. Controlling self-renewal and differentiation of stem cells via mechanical cues. Journal of Biomedicine and Biotechnology. 2012; 2012(797410):1-12. Crossref. PMID:23091358 PMCID:PMC3471035.
8. Paluch EK, Nelson CM, Biais N, Fabry B, Moeller J, Pruitt BL. Mechanotransduction: Use the force(s). BMC Biology. 2015; 13(1):1-14. Crossref. PMID:26141078 PMCID:PMC4491211.

9. Geiger B, Spatz J, Bershadsky A. Environmental sensing through focal adhesions. *Nature Reviews Molecular Cell Biology*. 2009; 10(1):21-33. Crossref. PMID:19197329.
10. Polo-Corrales L, Latorre-Esteves M, Ramirez-Vick JE. Scaffold Design for Bone Regeneration. *Journal Nanoscience Nanotechnology*. 2014 Jan; 14(1):1-42. Crossref.
11. Dado D, Levenberg S, Sagi M, Zemel A. Mechanical control of stem cell differentiation. *Regenerative Medicine*. 2012; 7(1):1-101. Crossref. PMID:22168501.
12. Leung DYM, Glagov S, Mathews MB, Uhl S, Brient LVO. Cyclic Stretching Stimulates Synthesis of Matrix Components by Arterial Smooth Muscle Cells in vitro. *Science*. 1976; 191(4226):475-7. Crossref. PMID:128820.
13. Toyoda T, Matsumoto H, Fujikawa K, Saito S, Inoue K. Tensile Load and the Metabolism of Anterior Cruciate Ligament Cells. *Clinical Orthopaedics and Related Research*. 1998; 353:247-55. Crossref. PMID:9728181.
14. Carter D, Beaupre G, Giori N, Helms J. Mechanobiology of skeletal regeneration. *Clinical Orthopaedics and Related Research*. 1998; 355:41-55. Crossref.
15. Claes LE, Heigele CA. Magnitudes of local stress and strain along bony surfaces predict the course and type of fracture healing. *Journal of Biomechanics*. 1999 Mar; 32(3):255-66. Crossref.
16. Lacroix D, Prendergast PJ. A mechano-regulation model for tissue differentiation during fracture healing: analysis of gap size and loading. *Journal of Biomechanics*. 2002 Sep; 35(9):1163-71. Crossref.
17. Jang J, Lee SW, Park SH, Shin JW, Mun C, Kim S. Combined Effects of Surface Morphology and Mechanical Straining Magnitudes on the Differentiation of Mesenchymal Stem Cells without Using Biochemical Reagents. *Journal of Biomedicine and Biotechnology*. 2011; p. 1-9. Crossref. PMID:21403908 PMCID:PMC3043320.
18. Park JS, Chu JSF, Cheng C, Chen F, Chen D, Li S. Differential effects of equiaxial and uniaxial strain on mesenchymal stem cells. *Biotechnology and Bioengineering*. 2004 Nov; 88(3):359-68. Crossref. PMID:15486942.
19. Kurpinski K, Chu J, Hashi C, Li S. Anisotropic mechanosensing by mesenchymal stem cells. *Proceedings of the National Academy of Sciences of the United States of America*. 2006 Oct; 103(44):16095-100. Crossref. PMID:17060641 PMCID:PMC1637542.
20. Haasper C, Jagodzinski M, Drescher M, Meller R, Wehmeier M, Krettek C. Cyclic strain induces FosB and initiates osteogenic differentiation of mesenchymal cells. *Experimental and Toxicologic Pathology*. 2008 Apr; 59(6):355-63. Crossref. PMID:18222075.
21. Friedl G, Schmidt H, Rehak I, Kostner G, Schauenstein K, Windhager R. Undifferentiated human mesenchymal stem cells (HMSCs) are highly sensitive to mechanical strain: transcriptionally controlled early osteo-chondrogenic response in vitro. *Osteoarthritis Cartilage*. 2007 Nov; 15(11):1293-300. Crossref. PMID:17977755.
22. Song G, Ju Y, Shen X, Luo Q, Shi Y, Qin J. Mechanical stretch promotes proliferation of rat bone marrow mesenchymal stem cells. *Colloids and Surfaces B: Biointerfaces*. 2007 Aug; 58(2):271-7. Crossref. PMID:17499488.
23. Chen D, Zhao M, Mundy GR. Bone morphogenetic proteins. *Growth factors*. 2004; 22(4):233-41. Crossref. PMID:15621726.
24. Sumanasinghe RD, Bernacki SH, Lobo EG. Osteogenic Differentiation of Human Mesenchymal Stem Cells on Bone Morphogenetic Protein (BMP-2) mRNA Expression. *Tissue Engineering*. 2006; 12(12):3459-65. Crossref. PMID:17518682.
25. Pfeiler TW, Sumanasinghe RD, Lobo EG. Finite element modeling of 3D human mesenchymal stem cell-seeded collagen matrices exposed to tensile strain. *Journal of Biomechanics*. 2008 Jul; 41(10):2289-96. Crossref. PMID:18539285 PMCID:PMC3947927.
26. Sumanasinghe RD, Pfeiler TW, Monteiro-Riviere NA, Lobo EG. Expression of proinflammatory cytokines by human mesenchymal stem cells in response to cyclic tensile strain. *Journal of Cellular Physiology*. 2009 Apr; 219(1):77-83. Crossref. PMID:19089992.
27. Kearney EM, Farrell E, Prendergast PJ, Campbell VA. Tensile strain as a regulator of mesenchymal stem cell

- osteogenesis. *Annals of Biomedical Engineering*. 2010 May; 38(5):1767-79. Crossref. PMID:20217480.
28. Lee JS, Ha L, Park J-H, Lim JY. Mechanical stretch suppresses BMP4 induction of stem cell adipogenesis via up regulating ERK but not through downregulating Smad or p38. *Biochemical and Biophysical Research Communications*. 2012 Feb; 418(2):278-83. Crossref. PMID:22266311.
  29. Hanson AD, Marvel SW, Bernacki SH, Banes AJ, van Aalst J, Loba EG. Osteogenic effects of rest inserted and continuous cyclic tensile strain on hASC lines with disparate osteodifferentiation capabilities. *Annals of Biomedical Engineering*. 2009 May; 37(5):955-65. Crossref. PMID:19229619.
  30. Charoenpanich A, Wall ME, Tucker CJ, Andrews DMK, Lalush DS, Dirschl DR. Cyclic Tensile Strain Enhances Osteogenesis and Angiogenesis in Mesenchymal Stem Cells from Osteoporotic Donors. *Tissue Engineering Part A*. 2014; 2(1-2):67-78. Crossref. PMID:23927731 PMID:PMC3875187.
  31. Lee S-K, Lee C-Y, Kook Y-A, Lee S-K, Kim E-C. Mechanical stress promotes odontoblastic differentiation via the heme oxygenase-1 pathway in human dental pulp cell line. *Life Science*. 2010 Jan; 86(3-4):107-14. Crossref. PMID:19951713.
  32. Subay R, Kaya H, Tarim B, Subay A, Cox C. Response of human pulpal tissue to orthodontic extrusive applications. *Journal of Endodontics*. 2001; 27(8):508-11. Crossref. PMID:11501587.
  33. Tang N, Zhao Z, Zhang L, Yu Q, Li J, Xu Z. Up-regulated osteogenic transcription factors during early response of human periodontal ligament stem cells to cyclic tensile strain. *Archives of Medical Science*. 2012 Jul; 8(3):422-30. Crossref. PMID:22851995 PMID:PMC3400899.
  34. Quinlan TAM, Sierad LN, Capulli AK, Firstenberg LE, Billiar KL. Combining dynamic stretch and tunable stiffness to probe cell mechanobiology in vitro. *PLoS One*. 2011 Jan; 6(8):23-272.
  35. Wingate K, Bonani W, Tan Y, Bryant SJ, Tan W. Compressive elasticity of three-dimensional nanofiber matrix directs mesenchymal stem cell differentiation to vascular cells with endothelial or smooth muscle cell markers. *Acta Biomaterialia*. 2012 Apr; 8(4):1440-9. Crossref. PMID:22266031 PMID:PMC3289764.
  36. Subramony SD, Su A, Yeager K, Lu HH. Combined Effects of Chemical Priming and Mechanical Stimulation on Mesenchymal Stem Cell Differentiation on Nanofiber Scaffolds. *Journal of Biomechanics*. 2014 Jun; 47(9):2189-96. Crossref. PMID:24267271 PMID:PMC4058785.
  37. Subramony SD, Dargis BR, Castillo M, Azeloglu EU, Tracey MS, Su A. The guidance of stem cell differentiation by substrate alignment and mechanical stimulation. *Biomaterials* [Internet]. 2013 Mar; 34(8):1942-53. Crossref. PMID:23245926 PMID:PMC3689925.
  38. Charoenpanich A, Wall ME, Tucker CJ, Andrews DMK, Lalush DS, Loba EG. Microarray analysis of human adipose-derived stem cells in three-dimensional collagen culture: osteogenesis inhibits bone morphogenic protein and Wnt signaling pathways, and cyclic tensile strain causes upregulation of proinflammatory cytokine regulators. *Tissue Engineering Part A*. 2011 Nov; 17(21-22):2615-27. Crossref. PMID:21767168 PMID:PMC3204199.
  39. Banka S, Mukudai Y, Yoshihama Y, Shirota T, Kondo S, Shintani S. A combination of chemical and mechanical stimuli enhances not only osteo-but also chondro-differentiation in adipose-derived stem cells. *Journal of Oral Biosciences*. 2012 Nov; 54(4):188-95. Crossref.
  40. Huang Y, Zheng L, Gong X, Jia X, Song W, Liu M. Effect of cyclic strain on cardiomyogenic differentiation of rat bone marrow derived mesenchymal stem cells. *PLoS One*. 2012 Jan; 7(4):1-34960. Crossref. PMID:22496879 PMID:PMC3319595.
  41. Baker BM, Shah RP, Huang AH, Mauck RL. Dynamic Tensile Loading Improves the Functional Properties of Mesenchymal Stem Cell-Laden. *Tissue Engineering Part A*. 2011; 17(9-10):1445-55. Crossref. PMID:21247342 PMID:PMC3079166.
  42. Leong WS, Wu SC, Pal M, Tay CY, Yu H, Li H. Cyclic tensile loading regulates human mesenchymal stem cell differentiation into neuron-like phenotype. *Journal of Tissue Engineering and Regenerative Medicine*. 2012; 6(s3):68-79. Crossref. PMID:22777815.
  43. Rathbone SR, Glossop JR, Gough JE, Cartmell SH. Cyclic tensile strain upon human mesenchymal stem cells in 2D and 3D culture differentially influences CCN2, WDR61 and BAHCC1 gene expression levels. *Journal of*



- the Mechanical Behavior of Biomedical Materials. 2012 Jul; 11:82-91. Crossref. PMID:22658157.
44. Qi M-C, Hu J, Zou S-J, Chen H-Q. Mechanical strain induces osteogenic differentiation: Cbfa1 and Ets-1 expression in stretched rat mesenchymal stem cells. *International Journal of Oral and Maxillofacial Surgery*. 2008 May; 37(5):453-8. Crossref. PMID:18272346.
  45. Huang C, Ogawa R. Effect of Hydrostatic Pressure on Bone Regeneration. *Tissue Engineering Part A*. 2012; 18(19):2106-13. Crossref. PMID:22607391.
  46. Shin HY, Schwartz EA, Bizios R, Gerritsen ME. Receptor-Mediated Basic Fibroblast Growth Factor Signaling Regulates Cyclic Pressure-Induced Human Endothelial Cell Proliferation. *Endothelium*. 2004; 11(5-6):285-91. Crossref. PMID:15763948.
  47. Maul TM, Chew DW, Nieponice A, Vorp DA. Mechanical stimuli differentially control stem cell behavior: morphology, proliferation, and differentiation. *Biomechanics and Modeling in Mechanobiology*. 2011 Dec; 10(6):939-53. Crossref. PMID:21253809 PMCID:PMC3208754.
  48. Ferraro JT, Daneshmand M, Bizios R, Rizzo V. Depletion of plasma membrane cholesterol dampens hydrostatic pressure and shear stress-induced mechanotransduction pathways in osteoblast cultures. *American Journal of Physiology-Cell Physiology*. 2004; 286:831-9. Crossref. PMID:14644772.
  49. Nagatomi J, Arulanandam BP, Metzger DW, Meunier A, Bizios R. Frequency- and Duration-Dependent Effects of Cyclic Pressure on Select Bone Cell Functions. *TISSUE Engineering*. 2001; 7(6):717-28. Crossref. PMID:11749729.
  50. Nagatomi J, Arulanandam BP, Metzger DW, Meunier A, Bizios R. Effects of Cyclic Pressure on Bone Marrow Cell Cultures. *Journal of Biomechanical Engineering*. 2002 May; 124(3):1-308.
  51. Nagatomi J, Arulanandam BP, Metzger DW, Meunier A, Bizios R. Cyclic Pressure Affects Osteoblast Functions Pertinent to Osteogenesis. *Annals of Biomedical Engineering*. 2003 Mar; 31:917-23. Crossref. PMID:12918906.
  52. Kang YG, Garcia M V, Marquez JC, Park SH, Oh MJ, Kim YM. Effects of various patterns of intermittent hydrostatic pressure on the osteogenic differentiation of mesenchymal stem cells. *Tissue Engineering and Regenerative Medicine*. 2014 Feb; 11(S1):32-9. Crossref.
  53. Haudenschild AK, Hsieh AH, Kapila S, Lotz JC. Pressure and distortion regulate human mesenchymal stem cell gene expression. *Annual Review of Biomedical Engineering*. 2009 Mar; 37(3):492-502. Crossref. PMID:19125331.
  54. Sah RL, Kim Y, Doong JH, Grodzinsky AJ, Plaas AHK, Sandy JD. Biosynthetic Response of Cartilage Explants to Dynamic Compression. *Journal of Orthopaedic Research*. 1989; 7(5):619-36. Crossref. PMID:2760736.
  55. Buschmann MD, Kim Y, Wong M, Frank E, Hunziker EB, Grodzinsky AJ. Stimulation of Aggrecan Synthesis in Cartilage Explants by Cyclic Loading Is Localized to Regions of High Interstitial Fluid Flow. *Archives of Biochemistry and Biophysics*. 1999; 366(1):1-7. Crossref. PMID:10334856.
  56. Fitzgerald JB, Jin M, Grodzinsky AJ. Shear and compression differentially regulate clusters of functionally related temporal transcription patterns in cartilage tissue. *Journal of Biological Chemistry*. 2006 Aug; 281(34):24095-103. Crossref. PMID:16782710.
  57. Alin M, Li Z, Stoddart MJ, Yao S-J. Chondrogenesis of human bone marrow mesenchymal stem cells in fibrin-polyurethane composites is modulated by frequency and amplitude of dynamic compression and shear stress. *Tissue Engineering Part A Tissue Engineering*. 2010; 16(2):575-84. Crossref. PMID:19737049.
  58. Pelaez D, Huang C-YC, Cheung HS. Cyclic compression maintains viability and induces chondrogenesis of human Mesenchymal stem cells in fibrin gel scaffolds. *Stem Cells and Development*. 2009; 18(1):93-102. Crossref. PMID:18399763.
  59. Park S-H, Sim WY, Min B-H, Yang SS, Khademhosseini A, Kaplan DL. Chip-based comparison of the osteogenesis of human bone marrow- and adipose tissue-derived mesenchymal stem cells under mechanical stimulation. *PLoS One*. 2012 Jan; 7(9):46689. Crossref. PMID:23029565 PMCID:PMC3460891.
  60. Zhang M, Chen F-M, Wang A-H, Chen Y-J, Lv X, Wu S. Estrogen and its receptor enhance mechanobiological effects in compressed bone mesenchymal stem cells. *Cells Tissues Organs*. 2012 Jan; 195(5):400-13. Crossref. PMID:21832815.
  61. Liu J, Zhao Z, Li J, Zou L, Shuler C, Zou Y. Hydrostatic pressures promote initial osteodifferentiation with

- ERK1/2 not p38 MAPK signaling involved. *Journal of Cellular Biochemistry*. 2009 May; 107(2):224-32. Crossref. PMID:19259952.
62. Liu J, Zhao Z, Zou L, Li J, Wang F, Li X, et al. Pressure-loaded MSCs during early osteodifferentiation promote osteoclastogenesis by increase of RANKL/OPG ratio. *Annals of Biomedical Engineering*. 2009 Apr; 37(4):794-802. Crossref. PMID:19148752.
  63. Zhang Y, Yang Z, Zhang H. Effect of Negative Pressure on Human Bone Marrow Mesenchymal Stem Cells In Vitro. *Connective Tissue Research*. 2010; 51:14-21. Crossref. PMID:20067412.
  64. Kim DH, Kim S-H, Heo S-J, Shin JW, Lee SW, Park SA. Enhanced differentiation of mesenchymal stem cells into NP-like cells via 3D co-culturing with mechanical stimulation. *Journal of Bioscience and Bioengineering*. 2009 Jul; 108(1):63-7. Crossref. PMID:19577195.
  65. Kim SY, Park SH, Shin JW, Kang YG, Jeon KJ, Hyun J-S. Mechanical stimulation and the presence of neighboring cells greatly affect migration of human mesenchymal stem cells. *Biotechnology Letter*. 2013 Nov; 35(11):1817-22. Crossref. PMID:23881314.
  66. Jeong JY, Park SH, Shin JW, Kang YG, Han K-H, Shin J-W. Effects of intermittent hydrostatic pressure magnitude on the chondrogenesis of MSCs with out biochemical agents under 3D co-culture. *Journal of Materials Science: Materials in Medicine*. 2012 Nov; 23(11):2773-81. Crossref. PMID:22802107.
  67. Dai J, Wang H, Liu G, Xu Z, Li F, Fang H. Dynamic compression and co-culture with nucleus pulposus cells promotes proliferation and differentiation of adipose-derived mesenchymal stem cells. *Journal of Biomechanics*. 2014 Mar; 47(5):966-72. Crossref. PMID:24529753.
  68. Meyer EG, Buckley CT, Steward J, Kelly DJ. The effect of cyclic hydrostatic pressure on the functional development of cartilaginous tissues engineered using bone marrow derived mesenchymal stem cells. *Journal of the Mechanical Behavior of Biomedical Materials*. 2011 Oct; 4(7):1257-65. Crossref. PMID:21783134.
  69. Mizuno S, Murphy GF, Ogawa R, Orgill DP. The effect of hydrostatic pressure on three-dimensional chondroinduction of human adipose-derived stem cells. *Tissue Engineering Part A Tissue Engineering*. 2009; 15(10):1-2937.
  70. Safshekan F, Tafazzoli-Shadpour M, Shokrgozar MA, Haghighipour N, Mahdian R, Hemmati A. Intermittent hydrostatic pressure enhances growth factor-induced chondroinduction of human adipose-derived mesenchymal stem cells. *Artificial Organs*. 2012 Dec; 36(12):1065-71. Crossref. PMID:22882542.
  71. Vinardell T, Rolfe RA, Buckley CT, Meyer EG, Ahearne M, Murphy P. Hydrostatic pressure acts to stabilise a chondrogenic phenotype in porcine joint tissue derived stem cells. *European Cells & Materials*. 2012; 23:121-34. Crossref. PMID:22370795.
  72. Puetzer J, Williams J, Gillies A, Bernacki SH, Lobo EG. The Effects of Cyclic Hydrostatic Pressure on Chondrogenesis and Viability of Human Adipose- and Bone Marrow-Derived Mesenchymal Stem Cells in Three-Dimensional Agarose Constructs. *Tissue Engineering Part A*. 2013; 19(1-2):299-306. Crossref. PMID:22871265 PMCID:PMC3530937.
  73. Carroll SF, Buckley CT, Kelly DJ. Cyclic hydrostatic pressure promotes a stable cartilage phenotype and enhances the functional development of cartilaginous grafts engineered using multipotent stromal cells isolated from bone marrow and in frapatellar fat pad. *Journal of Biomechanics*. 2014 Jun; 47(9):2115-21. Crossref. PMID:24377681.
  74. Karkhaneh A, Naghizadeh Z, Shokrgozar MA, Bonakdar S, Solouk A, Haghighipour N. Effects of hydrostatic pressure on biosynthetic activity during chondrogenic differentiation of MSCs in hybrid scaffolds. *The International Journal of Artificial Organs*. 2014 Feb; 37(2):142-8. Crossref. PMID:24619897.
  75. Wagner DR, Lindsey DP, Li KW, Tummala P, Chandran SE, Smith RL. Hydrostatic Pressure Enhances Chondrogenic Differentiation of Human Bone Marrow Stromal Cells in Osteochondrogenic Medium. *Annals of Biomedical Engineering*. 2008; 36(5):813-20. Crossref. PMID:18266109.
  76. Steward AJ, Steward AJ, Wagner DR, Kelly DJ. The pericellular environment regulates cytoskeletal development and the differentiation of mesenchymal stem cells and determines their response to hydrostatic pressure. *European Cells & Materials*. 2013; 25:167-78. Crossref. PMID:23389751.
  77. Liu L, Chen L, Mai Z, Peng Z, Yu K, Liu G. Cyclical compressive stress induces differentiation of rat primary



- mandibular condylar chondrocytes through phosphorylated myosin light chain II. *Molecular Medicine Reports*. 2016; 14(5):4293-300. Crossref. PMID:27748856.
78. Hess R, Douglas T, Myers KA, Rentsch B, Rentsch C, Worch H. Hydrostatic pressure stimulation of human mesenchymal stem cells seeded on collagen-based artificial extracellular matrices. *Journal of Biomechanical Engineering*. 2010 Feb; 132(2):1-21001. Crossref. PMID:20370238.
  79. Steward AJ, Thorpe SD, Vinardell T, Buckley CT, Wagner DR, Kelly DJ. Cell-matrix interactions regulate mesenchymal stem cell response to hydrostatic pressure. *Acta Biomaterialia*. 2012 Jun; 8(6):2153-9. Crossref. PMID:22426136.
  80. Reinwald Y, El Haj AJ. Hydrostatic pressure in combination with topographical cues affects the fate of bone marrow-derived human mesenchymal stem cells for bone tissue regeneration. *Journal of Biomedical Materials Research part A*. 2018; 106(3):629-40. Crossref. PMID:28984025 PMCid:PMC5813264.
  81. Padilla F, Puts R, Vico L, Raum K. Stimulation of bone repair with ultrasound: A review of the possible mechanic effects. *Ultrasonics*. 2014; 54:1125-45. Crossref. PMID:24507669.
  82. Claes L, Willie B. The enhancement of bone regeneration by ultrasound. *Progress in Biophysics and Molecular Biology*. 2007; 93:384-98. Crossref. PMID:16934857.
  83. Reher P, Elbeshir ENI, Harvey W, Meghji S, Harris M. The stimulation of bone formation in vitro by therapeutic ultrasound. *Ultrasound in Medicine & Biology*. 1997; 23(8):1251-8. Crossref.
  84. Park H, Yip MC, Chertok B, Kost J, Kobler JB, Langer R. Indirect low-intensity ultrasonic stimulation for tissue engineering. *Journal Tissue Engineering*. 2010; p. 1-973530. Crossref.
  85. Dyson M, Bookes M. Stimulation of bone repair by ultrasound. *Ultrasound in Medicine & Biology*. 1983; 2(9):61-6. PMID:6545743.
  86. Subramanian A, Turner JA., Budhiraja G, Thakurta SG, Whitney NP, Nudurupati SS. Ultrasonic Bioreactor as a Platform for Studying Cellular Response. *Tissue Engineering Part C Methods*. 2012; 19(3):244-55. Crossref. PMID:22873765 PMCid:PMC3557434.
  87. Scheven BAA, Shelton RM, Cooper PR, Walmsley AD, Smith AJ. The therapeutic ultra sound for dental tissue repair. *Medical Hypotheses*. 2009; 73(4):591-3. Crossref. PMID:19553029.
  88. Yang KH, Parvizi J, Wang SJ, Lewallen DG, Kinnick RR, Greenleaf JF. Exposure to low-intensity ultra sound increases aggrecan gene expression in a rat femur fracture model. *Journal of Orthopaedic Research*. 1996; 14:802-9. Crossref. PMID:8893775.
  89. Yang S-W, Kuo C-L, Chang SJ, Chen P-C, Lin YT, Manousakas I. Does Low-intensity pulsed ultrasound treatment repair articular cartilage injury? A rabbit model study. *BMC Musculoskelet Disord*. 2014; 15(1):1-36. Crossref. PMID:24507771 PMCid:PMC3923237.
  90. Louw TM, Budhiraja G, Viljoen HJ, Subramanian A. Mechanotransduction of Ultrasound is Frequency Dependent Below the Cavitation Threshold. *Ultrasound in Medicine and Biology*. 2013; 39(7):1303-19. Crossref. PMID:23562015 PMCid:PMC4183372.
  91. Marvel S, Okrasinski S, Bernacki SH, Lobo E, Dayton PA. The development and validation of a lipus system with preliminary observations of ultrasonic effects on human adult stem cells. *IEEE Transactions on Ultrasonics, Ferroelectrics, and Frequency*. 2010; 57(9):1-84. Crossref.
  92. Leung K-S, Lee W-S, Tsui H-F, Liu PP-L, Cheung W-H. Complex tibial fracture outcomes following treatment with low-intensity pulsed ultrasound. *Ultrasound in Medicine & Biology*. 2004; 30(3):389-95. Crossref. PMID:15063521.
  93. Walker NA, Denegar CR, Preische J. Low-intensity pulsed ultrasound and pulsed electromagnetic field in the treatment of tibial fractures: A systematic review. *Journal of Athletic Training*. 2007; 42(4):530-5. PMID:18174942 PMCid:PMC2140080.
  94. Schofer MD, Block JE, Aigner J, Schmelz A. Improved healing response in delayed unions of the tibia with low-intensity pulsed ultrasound: results of a randomized sham-controlled trial. *BMC Musculoskelet Disord*. 2010; 11(1):1-229. Crossref. PMID:20932272 PMCid:PMC2958986.
  95. Ying Z, Lin T, Yan S. Low-intensity pulsed ultra sound therapy: a potential strategy to stimulate tendon-bone junction healing. *Journal of Zhejiang University Science B*. 2012; 13(12):955-63. Crossref. PMID:23225850 PMCid:PMC3520449.

96. Cheung WH, Chin WC, Qin L, Leung KS. Low intensity pulsed ultrasound enhances fracture healing in both ovariectomy-induced osteoporotic and age-matched normal bones. *Journal of Orthopaedic Research*. 2012; 30:129-36. Crossref. PMID:21688313.
97. Yan SG, Huang LY, Cai XZ. Low-intensity pulsed ultrasound: A potential non-invasive therapy for femoral head osteonecrosis. *Medical Hypotheses*. 2011; 76(1):4-7. Crossref. PMID:20826064.
98. Warden SJ, Fuchs RK, Kessler CK, Avin KG, Cardinal RE, Stewart RL. Ultrasound produced by a conventional therapeutic ultrasound unit accelerates fracture repair. *Physical Therapy*. 2006; 86:1118-27. Crossref.
99. Hu J, Qu J, Xu D, Zhang T, Qin L, Lu H. Combined application of low-intensity pulsed ultrasound and functional electrical stimulation accelerates bone-tendon junction healing in a rabbit model. *Journal of Orthopaedic Research*. 2014; p. 204-9. Crossref. PMID:24136665.
100. Salem KH, Schmelz A. Low-intensity pulsed ultrasound shortens the treatment time in tibial distraction osteogenesis. *International Orthopaedics*. 2014; 38:1477-82. Crossref. PMID:24390009 PMCID:PMC4071501.
101. Lee HJ, Choi BH, Min BH, Son YS, Park SR. Low-intensity ultrasound stimulation enhances chondrogenic differentiation in alginate culture of mesenchymal stem cells. *Artificial Organs*. 2006; 30(9):707-15. Crossref. PMID:16934100.
102. Lee HJ, Choi BH, Min B-H, Park SR. Low-intensity ultrasound inhibits apoptosis and enhances viability of human mesenchymal stem cells in three-dimensional alginate culture during chondrogenic differentiation. *Tissue Engineering*. 2007; 13(5):1049-57. Crossref. PMID:17428192.
103. Cui JH, Park K, Park SR, Min B-H. Effects of low-intensity ultrasound on chondrogenic differentiation of mesenchymal stem cells embedded in polyglycolic acid: an in vivo study. *Tissue Engineering*. 2006; 12(1):75-82. Crossref. PMID:16499444.
104. Ebisawa K, Hata K-I, Okada K, Kimata K, Ueda M, Torii S. Ultrasound Enhances Transforming Growth Factor-Mediated Chondrocyte Differentiation of Human Mesenchymal Stem Cells. *Tissue Engineering*. 2004; 10(5/6):921-9. Crossref. PMID:15265310.
105. Choi WH, Choi BH, Min B-H, Park SR. Low-intensity ultrasound increased colony forming unit-fibroblasts of mesenchymal stem cells during primary culture. *Tissue Engineering Part C Methods*. 2011; 17(5):517-26. Crossref. PMID:21171932.
106. Angle SR, Sena K, Sumner DR, Virdi AS. Osteogenic differentiation of rat bone marrow stromal cells by various intensities of low-intensity pulsed ultrasound. *Ultrasonics*. 2011; 51(3):1-2818. Crossref. PMID:20965537.
107. Kumagai K, Takeuchi R, Ishikawa H, Yamaguchi Y, Fujisawa T, Kuniya T. Low-intensity pulsed ultrasound accelerates fracture healing by stimulation of recruitment of both local and circulating osteogenic progenitors. *Journal of Orthopaedic Research*. 2012; 30(9):1516-21. Crossref. PMID:22419401.
108. Uddin SMZ, Qin Y-X. Enhancement of osteogenic differentiation and proliferation in human mesenchymal stem cells by a modified low intensity ultrasound stimulation under simulated microgravity. *PLoS One*. 2013; 8(9):1-73914. Crossref. PMID:24069248 PMCID:PMC3772078.
109. Wang Y, Peng W, Liu X, Zhu M, Sun T, Peng Q. Study of bilineage differentiation of human-bone-marrow-derived mesenchymal stem cells in oxidized sodium alginate/N-succinyl chitosan hydrogels and synergistic effects of RGD modification and low-intensity pulsed ultrasound. *Acta Biomaterialia*. 2014; 10(6):2518-28. Crossref. PMID:24394634.
110. Thakurta SG, Budhiraja G, Subramanian A. Growth factor and ultrasound-assisted bioreactor synergism for human mesenchymal stem cell chondrogenesis. *Journal of Tissue Engineering*. 2015; p. 1-6. Crossref.
111. Lim K, Kim J, Seonwoo H, Park SH, Choung PH, Chung JH. In vitro effects of low-intensity pulsed ultrasound stimulation on the osteogenic differentiation of human alveolar bone-derived mesenchymal stem cells for tooth tissue engineering. *BioMed Research International*. 2013; p. 269-724.
112. Hu B, Zhang Y, Zhou J, Li J, Deng F, Wang Z. Low-intensity pulsed ultrasound stimulation facilitates osteogenic differentiation of human periodontal ligament cells. *PLoS One*. 2014; 9(4):1-10. Crossref. PMID:24743551 PMCID:PMC3990585.
113. Ghebes CA, Braham MVJ, Zeegers AVCM, Renard AJS, Fernandes H, Saris DBF. Means of enhancing bone fracture healing: Optimal cell source, isolation methods and acoustic stimulation. *BMC Biotechnology*.

- 2016; 16(1):1-14. Crossref. PMID:27955656  
PMCID:PMC5154008.
114. Adamo L, Garcia-Carda-AG. Directed stem cell differentiation by fluid mechanical forces. *Antioxidants & Redox Signaling*. 2011 Sep; 15(5):1463-73. Crossref. PMID:21294651 PMCID:PMC3144423.
115. Prendergast P, Huiskes RKS. Biophysical stimuli on cells during tissue differentiation at implant interfaces. *Journal of Biomechanics*. 1997; 30(6):539-48. Crossref.
116. Hayward LNM, Morgan EF. Assessment of a mechano-regulation theory of skeletal tissue differentiation in an in vivo model of mechanically induced cartilage formation. *Biomechanics and Modeling in Mechanobiology*. 2009 Dec; 8(6):447-55. Crossref. PMID:19156455 PMCID:PMC2999671.
117. Stops JF, Heraty KB, Browne M, O'Brien FJ, McHugh PE. A prediction of cell differentiation and proliferation within a collagen-glycosaminoglycan scaffold subjected to mechanical strain and perfusive fluid flow. *Journal of Biomechanics*. 2010 Mar; 43(4):618-26. Crossref. PMID:19939388.
118. Luo W, Xiong W, Zhou J, Fang Z, Chen W, Fan Y, et al. Laminar shear stress delivers cell cycle arrest and anti-apoptosis to mesenchymal stem cells. *Acta Biochimica et Biophysica Sinica*. 2011; 43(3):210-6. Crossref. PMID:21335336.
119. Zarubin T, Han J. Activation and signaling of the p38 MAP kinase pathway. *Cell Research*. 2005; 15(1):11-8. Crossref. PMID:15686620.
120. Coulthard LR, White DE, Jones DL, McDermott MF, Burchill SA. p38MAPK: stress responses from molecular mechanisms to therapeutics. *Trends in Molecular Medicine*. 2009; 15(8):369-79. Crossref. PMID:19665431 PMCID:PMC3016890.
121. Grellier M, Bareille R, Bourget C. Responsiveness of human bone marrow stromal cells to shear stress. *Journal of Tissue Engineering and Regenerative Medicine*. 2009; 3:302-9. Crossref. PMID:19283726.
122. Fujita T, Azuma Y, Fukuyama R, Hattori Y, Yoshida C, Koida M, et al. Runx2 induces osteoblast and chondrocyte differentiation and enhances their migration by coupling with PI3K-Akt signaling. *Journal of Cell Biology*. 2004; 166(1):85-95. Crossref. PMID:15226309 PMCID:PMC2172136.
123. Liu L, Shao L, Li B, Zong C, Li J, Zheng Q. Extracellular signal-regulated kinase1/2 activated by fluid shear stress promotes osteogenic differentiation of human bone marrow-derived mesenchymal stem cells through novel signaling pathways. *The International Journal of Biochemistry & Cell Biology*. 2011 Nov; 43(11):1591-601. Crossref. PMID:21810479.
124. Yourek G, McCormick SM, Mao JJ, Reilly GC. Shear stress induces osteogenic differentiation of human mesenchymal stem cells. *Regenerative Medicine*. 2010 Sep; 5(5):713-24. Crossref. PMID:20868327 PMCID:PMC4093787.
125. McBride SH, Falls T, Knothe Tate ML. Modulation of stem cell shape and fate B: mechanical modulation of cell shape and gene expression. *Tissue Engineering Part A*. 2008 Sep; 14(9):1573-80. Crossref.
126. Kim DH, Heo S-J, Kim S-H, Shin JW, Park SH, Shin J-W. Shear stress magnitude is critical in regulating the differentiation of mesenchymal stem cells even with endothelial growth medium. *Biotechnology Letter*. 2011 Dec; 33(12):2351-9. Crossref. PMID:21805363.
127. Zhang H, Kay A, Forsyth NR, Liu K-K, El Haj AJ. Gene expression of single human mesenchymal stem cell in response to fluid shear. *Journal Tissue Engineering [Internet]*. 2012; 3(1):1-8. Crossref. PMID:22798982 PMCID:PMC3394398.
128. Glossop JR, Cartmell SH. Effect of fluid flow-induced shear stress on human mesenchymal stem cells: differential gene expression of IL1B and MAP3K8 in MAPK signaling. *Gene Expression Patterns*. 2009 Jun; 9(5):381-8. Crossref. PMID:19272346.
129. Glossop JR, Cartmell SH. Tensile strain and magnetic particle force application do not induce MAP3K8 and IL-1B differential gene expression in a similar manner to fluid shear stress in human mesenchymal stem cells. *Journal of Tissue Engineering and Regenerative Medicine*. 2010; 4:577-9. Crossref. PMID:20603871.
130. Huang Y, Jia X, Bai K, Gong X, Fan Y. Effect of fluid shear stress on cardiomyogenic differentiation of rat bone marrow mesenchymal stem cells. *Archives of Medical Research*. 2010 Oct; 41(7):497-505. Crossref. PMID:21167388.
131. Schatti O, Grad S, Goldhahn J, Salzmann G, Li Z, Alini M. A combination of shear and dynamic compression

- leads to mechanically induced chondrogenesis of human mesenchymal stem cells. *European Cells & Materials*. 2011; 22:214-25. Crossref. PMID:22048899.
132. Li Z, Yao S, Alini M, Stoddart M. Chondrogenesis of human bone marrow mesenchymal stem cells in fibrin-polyurethane composites is modulated by frequency and amplitude of dynamic compression and shear stress. *Tissue Engineering Part A*. 2010; 16(2):575-84. Crossref. PMID:19737049.
  133. Janeczek Portalska K, Leferink A, Groen N, Fernandes H, Moroni L, van Blitterswijk C, et al. Endothelial differentiation of mesenchymal stromal cells. *PLoS One*. 2012 Jan; 7(10):1-46842. Crossref. PMID:23056481 PMCid:PMC3464214.
  134. Dong J, Gu Y, Li C, Wang C, Feng Z, Qiu R. Response of mesenchymal stem cells to shear stress in tissue-engineered vascular grafts. *Acta Pharmacologica Sinica*. 2009 May; 30(5):530-6. Crossref. PMID:19417732 PMCid:PMC4002825.
  135. Bassaneze V, Barauna V, Lavini-Ramos C, Kalil J, Schettert I, Miyakawa A. Shear stress induces nitric oxide-mediated vascular endothelial growth factor production in human adipose tissue mesenchymal stem cells. *Stem Cells and Development*. 2010; 19(3):371-8. Crossref. PMID:19754225.
  136. Uzer G, Pongkitwitoon S, Ete Chan M, Judex S. Vibration induced osteogenic commitment of mesenchymal stem cells is enhanced by cytoskeletal remodeling but not fluid shear. *Journal of Biomechanics*. 2013 Sep; 46(13):2296-302. Crossref. PMID:23870506 PMCid:PMC3777744.
  137. Liu L, Yu B, Chen J, Tang Z, Zong C, Shen D. Different effects of intermittent and continuous fluid shear stresses on osteogenic differentiation of human mesenchymal stem cells. *Biomechanics and Modeling in Mechanobiology*. 2012 Mar; 11(3-4):391-401. Crossref. PMID:21633819.
  138. Sharp L, Lee YW, Goldstein AS. Effect of low-frequency pulsatile flow on expression of osteoblastic genes by bone marrow stromal cells. *Annals of Biomedical Engineering*. 2009 Mar; 37(3):445-53. Crossref. PMID:19130228.
  139. Kim J, Ma T. Bioreactor strategy in bone tissue engineering: pre-culture and osteogenic differentiation under two flow configurations. *Tissue Engineering Part A*. 2012; 18(21-22):2354-64. Crossref. PMID:22690750 PMCid:PMC3482853.
  140. Zhong W, Tian K, Zheng X, Li L, Zhang W, Wang S. Mesenchymal stem cell and chondrocyte fates in a multi-shear microdevice are regulated by Yes-associated protein. *Stem Cells Development*. 2013 Jul; 22(14):2083-93. Crossref. PMID:23442010.
  141. Lim K-T, Kim J, Seonwoo H, Chang JU, Choi H, Hexiu J. Enhanced osteogenesis of human alveolar bone-derived mesenchymal stem cells for tooth tissue engineering using fluid shear stress in a rocking culture method. *Tissue Engineering Part C Methods*. 2013 Feb; 19(2):128-45. Crossref. PMID:23088630.
  142. Delaine-Smith RM, MacNeil S, Reilly GC. Matrix production and collagen structure are enhanced in two types of osteogenic progenitor cells by a simple fluid shear stress stimulus. *European Cells & Materials*. 2012 Jan; 24:162-74. Crossref. PMID:22865228.
  143. Zheng L, Chen L, Chen Y, Gui J, Li Q, Huang Y. The effects of fluid shear stress on proliferation and osteogenesis of human periodontal ligament cells. *Journal of Biomechanics*. 2016; 49(4):572-9. Crossref. PMID:26892895.
  144. Lim K-T, Jin H, Seonwoo H, Kim H-B, Kim J, Kim J-W. Physical Stimulation-Based Osteogenesis: Effect of Secretion on Fluid Dynamic Shear Stress of Human Alveolar Bone-Derived Mesenchymal Stem Cells. *IEEE Transactions on NanoBioscience*. 2016; 15(8):881-90.
  145. Stavenschi E, Labour MN, Hoey DA. Oscillatory fluid flow induces the osteogenic lineage commitment of mesenchymal stem cells: The effect of shear stress magnitude, frequency, and duration. *Journal Biomechanics*. 2017; 55(8):99-106. Crossref. PMID:28256244.
  146. Vetsch JR, Betts DC, Mu R, Hofmann S. Flow velocity-driven differentiation of human mesenchymal stromal cells in silk fibroin scaffolds: A combined experimental and computational approach. *PLoS One*. 2017; 12(7):1-17. Crossref. PMID:28686698 PMCid:PMC5501602.
  147. Hartshorne E. On the causes and treatment of pseudarthrosis, and especially of that form of it sometimes called supernumerary joint. *American Journal of Medicine*. 1841; 1:121-56. Crossref.



148. Duchenne G. De l'électrisation localisée et de son application à la pathologie et à la thérapeutique. 2nd edition. Paris: Baillière. 1855.
149. Lente R. Cases of ununited fracture treated by electricity. New York State Journal of Medicine. 1850; 5:317-9.
150. Yasuda I. Dynamic Callus and Electric Callus. The Journal of Bone and Joint Surgery. 1955; 37:12-92.
151. Yasuda I. Piezoelectricity of Living Bone. The Journal of Bone and Joint Surgery. 1953; 53:1-325.
152. Yasuda I, Nagayama H, Kato T, Hara O, Okada K, Noguchi K, et al. Fundamental problems in the treatment of fracture. Journal of Kyoto Medical Society. 1953; 4:395-406.
153. Yasuda I, Noguchi K, Iida H. Application of Electrical Callus. Fuji Printing, Sapporo. 1984; p. 145-55. PMID:6727033.
154. Fukada E, Yasuda I. On the Piezoelectric Effect of Bone. Journal of the Physical Society of Japan. 1957; 12(10):1-1158. Crossref.
155. Bassett AL, Becker RO. Generation of Electric Potentials by Bone in Response to Mechanical Stress. Science. 1962; 137(3535):1063-4. Crossref. PMID:13865637.
156. Gan JC, Glazer PA. Electrical stimulation therapies for spinal fusions: current concepts. European Spine Journal. 2006 Sep; 15(9):1301-11. Crossref. PMID:16604354 PMCid:PMC2438580.
157. Bassett C, Pawluck R, Becker R. Effects of electrical currents on bone in vivo. Nature. 1964; 4:652-4. Crossref.
158. Shamos MH, Lavine LS, Shamos MI. Piezoelectric Effect in Bone. Nature. 1963; 197(4862):1-81. Crossref.
159. O'Connor B., Charlton HM, Currey JD, Kirby DRS, Woods C. Effect of electric Current on Bone in vivo. Nature. 1969; 222:162-3. Crossref. PMID:5777036.
160. Marino A, Becker RO. Piezoelectric effect and growth control in bone. Nature. 1970; 228:473-4. Crossref. PMID:5482504.
161. Richez J, Chamay, Bieler L. Bone changes due to pulses of direct electric microcurrent. Virchows Archiv. A, Pathology. Pathologische Anatomie. 1972 Jan; 357(1):11-8. Crossref. PMID:4628347.
162. Supronowicz PR, Ajayan PM, Ullmann KR, Arulanandam BP, Metzger DW, Bizios R. Novel current-conducting composite substrates for exposing osteoblasts to alternating current stimulation. Journal of Biomedical Materials Research Part A. 2002; 59(3):499-506. Crossref. PMID:11774308.
163. Friedenbergs Z, MC H, Brighton C. Healing of a non-union of the medial malleolus by means of direct current: A case report. The Journal of Trauma and Acute Care Surgery. 1971; 11:883-4. Crossref.
164. Dwyer AF, Wickham G. Direct current stimulation in spinal fusion. The Medical Journal of Australia. 1974; 1(3):73-5. PMID:4544556.
165. Sun S, Titushkin I, Cho M. Regulation of mesenchymal stem cell adhesion and orientation in 3D collagen scaffold by electrical stimulus. Bioelectrochemistry. 2006 Oct; 69(2):133-41. Crossref. PMID:16473050.
166. Zhao Z, Watt C, Karystinou A, Roelofs AJ, McCaig CD, Gibson IR. Directed migration of human bone marrow mesenchymal stem cells in a physiological direct current electric field. European Cells & Materials. 2011 Jan; 22:344-58. Crossref. PMID:22125259.
167. Sundelacruz S, Li C, Choi YJ, Levin M, Kaplan DL. Bioelectric modulation of wound healing in a 3D in vitro model of tissue-engineered bone. Biomaterials. 2013 Sep; 34(28):6695-705. Crossref. PMID:23764116 PMCid:PMC3724996.
168. Hronik-Tupaj M, Rice WL, Cronin-Golomb M, Kaplan DL, Georgakoudi I. Osteoblastic differentiation and stress response of human mesenchymal stem cells exposed to alternating current electric fields. Biomedical Engineering Online. 2011 Jan; 10(1):1-9. Crossref. PMID:21269490 PMCid:PMC3039627.
169. Tandon N, Goh B, Marsano A, Chao P-HG, Montouri-Sorrentino C, Gimble J, et al. Alignment and elongation of human adipose-derived stem cells in response to direct-current electrical stimulation. Conference Proceeding Engineering in Medicine and Biology Society. 2009 Jan; p. 6517-21. Crossref.
170. McCullen SD, Lubischer JL, McQuilling JP, Clarke LI, Grossfeld RM, Lobo EG. Application of Low-Frequency Alternating Current Electric Fields Via Interdigitated Electrodes: Effects on Cellular Viability, Cytoplasmic. Tissue Engineering Part C. 2010; p. 1-10.
171. Griffin M, Iqbal SA, Sebastian A, Colthurst J, Bayat A. Degenerate wave and capacitive coupling increase human MSC invasion and proliferation while reducing cytotoxicity in an in vitro wound healing model. PLoS One. 2011 Jan; 6(8):1-23404. Crossref. PMID:21858102 PMCid:PMC3156742.

172. Park JS, Yang HN, Woo DG, Jeon SY, Do H-J, Huh S-H, et al. Exogenous Nurr1 gene expression in electrically-stimulated human MSCs and the induction of neurogenesis. *Biomaterials*. 2012 Oct; 33(29):7300-8. Crossref. PMID:22800541.
173. Mooney E, Mackle JN, Blond DJ-P, O'Cearbhaill E, Shaw G, Blau WJ. The electrical stimulation of carbon nanotubes to provide a cardiomimetic cue to MSCs. *Biomaterials*. 2012 Sep; 33(26):6132-9. Crossref. PMID:22681974.
174. Crowder SW, Liang Y, Rath R, Park AM, Maltais S, Pintauro PN. Poly ( $\epsilon$ -caprolactone)-carbon nanotube composite scaffolds for enhanced cardiac differentiation of human mesenchymal stem cells. *Nanomedicine (Lond)*. 2013; 8(11):1-20. Crossref. PMID:23530764 PMCid:PMC3809159.
175. Wen L, Zhang C, Nong Y, Yao Q, Song Z. Mild electrical pulse current stimulation upregulates S100A4 and promotes cardiogenesis in MSC and cardiac myocytes coculture monolayer. *Cell Biochemistry and Biophysics*. 2013 Jan; 65(1):43-55. Crossref. PMID:22941361.
176. Matsumoto M, Imura T, Fukazawa T, Sun Y, Takeda M, Kajiume T. Electrical stimulation enhances neurogenin 2 expression through  $\beta$ -catenin signaling pathway of mouse bone marrow stromal cells and intensifies the effect of cell transplantation on brain injury. *Neuroscience Letter*. 2013 Jan; 533:71-6. Crossref. PMID:23142721.
177. Fathi E, Farahzadi R. Zinc Sulphate Mediates the Stimulation of Cell Proliferation of Rat Adipose Tissue-Derived Mesenchymal Stem Cells Under High Intensity of EMF Exposure. *Biological Trace Element Research*. 2017; p. 1199-4. Crossref.
178. Jazayeri M, Sc M, Shokrgozar MA, Haghighipour N. Effects of Electromagnetic Stimulation on Gene Expression of Mesenchymal Stem Cells and Repair of Bone Lesions. *Cell Journal*. 2017; 19(1):34-44. PMID:28367415.
179. Hess R, Jaeschke A, Neubert H, Hintze V, Moeller S, Schnabelrauch M. Synergistic effect of defined artificial extracellular matrices and pulsed electric fields on osteogenic differentiation of human MSCs. *Biomaterials*. 2012 Dec; 33(35):8975-85. Crossref. PMID:22995709.
180. Creecy CM, Neill CFO, Arulanandam BP, Sylvia VL, Navara CS, Bizios R. Mesenchymal Stem Cell Osteodifferentiation in Response to Alternating Electric Current. *Tissue Engineering Part A*. 2013; 19(3-4):467-74. Crossref. PMID:23083071 PMCid:PMC3542886.
181. Jamal D, De Guzman RC. Silicone Substrate with Collagen and Carbon Nanotubes Exposed to Pulsed Current for MSC Osteodifferentiation. *International Journal Biomaterials*. 2017; p. 1-9. Crossref. PMID:28912813 PMCid:PMC5587965.
182. Ravikumar K, Boda SK, Basu B. Synergy of substrate conductivity and intermittent electrical stimulation towards osteogenic differentiation of human mesenchymal stem cells. *Bioelectrochemistry*. 2017; 116:52-64. Crossref. PMID:28463692.
183. Bassett C, Pawluk R, Pilla A. Acceleration of fracture repair by electromagnetic fields. A surgically noninvasive method. *Annals of the New York Academy of Sciences*. 1974; 238:242-62. Crossref. PMID:4548330.
184. Bassett C, Pilla A, Pawluk R. A non-operative salvage of surgically-resistant pseudarthroses and non-unions by pulsing electromagnetic fields. A preliminary report. *Clinical Orthopaedics and Related Research*. 1977; 124:128-43. PMID:598067.
185. Bassett C, Mitchell S, Gaston S. Pulsing electromagnetic field treatment in ununited fractures and failed arthrodeses. *JAMA*. 1982; 24(5):623-8. Crossref.
186. Heckman J, Ingram A, Loyd R, Jr LJ, Mayer P. Nonunion treatment with pulsed electromagnetic fields. *Clinical Orthopaedics and Related Research*. 1981; 161:58-66. Crossref.
187. De Mattei M, Caruso A, Traina GC, Pezzetti F, Baroni T, Sollazzo V. Correlation between pulsed electromagnetic fields exposure time and cell proliferation increase in human osteosarcoma cell lines and human normal osteoblast cells in vitro. *Bioelectromagnetics*. 1999 Jan; 20(3):177-82. Crossref.
188. Lohmann CH, Schwartz Z, Liu Y, Guerkov H, Dean DD, Simon B. Pulsed electromagnetic field stimulation of MG63 osteoblast-like cells affects differentiation and local factor production. *Journal Orthopaedic Research*. 2000 Jul; 18(4):637-46. Crossref. PMID:11052501.
189. Lohmann CH, Schwartz Z, Liu Y, Li Z, Simon BJ, Sylvia VL. Pulsed electromagnetic fields affect phenotype and connexin 43 protein expression in MLO-Y4 osteocyte-like cells and ROS 17/2.8 osteoblast-like cells.



- Journal Orthopaedic Research. 2003 Mar; 21(2):326-34. Crossref.
190. Chang WH-S, Chen L-T, Sun J-S, Lin F-H. Effect of pulse-burst electromagnetic field stimulation on osteoblast cell activities. *Bioelectromagnetics*. 2004 Sep; 25(6):457-65. Crossref. PMID:15300732.
  191. Panagopoulos DJ, Karabarbounis A, Margaritis LH. Mechanism for action of electromagnetic fields on cells. *Biochemical and Biophysical Research Communications*. 2002 Oct 18; 298(1):95-102. Crossref.
  192. Deng XL, Lau CP, Lai K, Cheung KF, Lau GK, Li GR. Cell cycle-dependent expression of potassium channels and cell proliferation in rat mesenchymal stem cells from bone marrow. *Cell Proliferation*. 2007 Oct; 40(5):656-70. Crossref. PMID:17877608.
  193. Garner AL, Chen G, Chen N, Sridhara V, Kolb JF, Swanson RJ. Ultrashort electric pulse induced changes in cellular dielectric properties. *Biochemical and Biophysical Research Communications*. 2007 Oct 12; 362(1):139-44.
  194. Soda A, Ikehara T, Kinouchi Y, Yoshizaki K. Effect of exposure to an extremely low frequency-electromagnetic field on the cellular collagen with respect to signaling pathways in osteoblast-like cells. *The Journal of Medical Investigation*. 2008 Aug; 55(3-4):267-78. Crossref. PMID:18797142.
  195. Schwartz Z, Simon BJ, Duran MA, Barabino G, Chaudhri R, Boyan BD. Pulsed electromagnetic fields enhance BMP-2 dependent osteoblastic differentiation of human mesenchymal stem cells. *Journal Orthopaedic Research*. 2008 Sep; 26(9):1250-5. Crossref. PMID:18404656.
  196. Tsai M-T, Li W-J, Tuan RS, Chang WH. Modulation of osteogenesis in human mesenchymal stem cells by specific pulsed electromagnetic field stimulation. *Journal Orthopaedic Research*. 2009 Sep; 27(9):1169-74. Crossref. PMID:19274753 PMCID:PMC2746855.
  197. Yang Y, Tao C, Zhao D, Li F, Zhao W, Wu H. EMF acts on rat bone marrow mesenchymal stem cells to promote differentiation to osteoblasts and to inhibit differentiation to adipocytes. *Bioelectromagnetics [Internet]*. 2010 May; 31(4):277-85. PMID:20041434.
  198. Zhong C, Zhang X, Xu Z, He R. Effects of Low-Intensity Electromagnetic Fields on the. *Physical Therapy*. 2012; 92(9):1208-19. Crossref. PMID:22577063.
  199. Ceccarelli G, Bloise N, Mantelli M, Gastaldi G, Fassina L, De Angelis MGC. A comparative analysis of the in vitro effects of pulsed electromagnetic field treatment on osteogenic differentiation of two different mesenchymal cell lineages. *Biores Open Access*. 2013 Aug; 2(4):283-94. Crossref. PMID:23914335 PMCID:PMC3731679.
  200. Lim K, Hexiu J, Kim J, Seonwoo H, Cho WJ, Choung P-H. Effects of electromagnetic fields on osteogenesis of human alveolar bone-derived mesenchymal stem cells. *BioMed Research International*. 2013 Jan; p. 1-296019. Crossref. PMID:23509796 PMCID:PMC3581241.
  201. Zhao D, Wu H, Li F, Li R, Tao C. Electromagnetic field change the expression of osteogenesis genes in murine bone marrow mesenchymal stem cells. *Journal of Huazhong University of Science and Technology. Medical Sciences*. 2008 Apr; 28(2):152-5. Crossref. PMID:18480985.
  202. Sun L-Y, Hsieh D-K, Yu T-C, Chiu H-T, Lu S-F, Luo G-H. Effect of pulsed electromagnetic field on the proliferation and differentiation potential of human bone marrow mesenchymal stem cells. *Bioelectromagnetics*. 2009 May; 30(4):251-60. Crossref. PMID:19204973.
  203. Sun L-Y, Hsieh D-K, Lin P-C, Chiu H-T, Chiou T-W. Pulsed electromagnetic fields accelerate proliferation and osteogenic gene expression in human bone marrow mesenchymal stem cells during osteogenic differentiation. *Bioelectromagnetics*. 2010 Apr; 31(3):209-19. PMID:19866474.
  204. Yan J, Dong L, Zhang B, Qi N. Effects of extremely low-frequency magnetic field on growth and differentiation of human mesenchymal stem cells. *Electromagnetic Biology and Medicine*. 2010 Dec; 29(4):165-76. Crossref. PMID:20923323.
  205. Jaiswal RK, Jaiswal N, Bruder SP, Mbalaviele G, Marshak DR, Pittenger MF. Adult human mesenchymal stem cell differentiation to the osteogenic or adipogenic lineage is regulated by mitogen-activated protein kinase. *Journal of Biological Chemistry*. 2000; 275(13):9645-52. Crossref. PMID:10734116.
  206. Jansen JHW, Weyts FAA, Westbroek I, Jahr H, Chiba H, Pols HAP. Stretch-induced phosphorylation of ERK1/2 depends on differentiation stage of osteoblasts. *Journal of Cellular Biochemistry*. 2004 Oct; 93(3):542-51. Crossref. PMID:15378606.
  207. Nie K, Henderson. MAP kinase activation in cells exposed to a 60 Hz electromagnetic field. *Journal of Cellular Biochemistry*. 2003 Dec; 90(6):1197-206. Crossref. PMID:14635193.

208. Jansen JHW, van der Jagt OP, Punt BJ, Verhaar JAN, van Leeuwen JPTM, Weinans H, et al. Stimulation of osteogenic differentiation in human osteoprogenitor cells by pulsed electromagnetic fields: an in vitro study. *BMC Musculoskeletal Disorders*. 2010 Jan; 11:1-188. Crossref. PMID:20731873 PMCID:PMC2936347.
209. Mayer-Wagner S, Passberger A, Sievers B, Aigner J, Summer B, Schiergens TS. Effects of low frequency electromagnetic fields on the chondrogenic differentiation of human mesenchymal stem cells. *Bioelectromagnetics*. 2011 May; 32(4):283-90. Crossref. PMID:21452358.
210. Ongaro A, Pellati A, Setti S, Masieri FF, Aquila G, Fini M. Electromagnetic fields counteract IL-1 b activity during chondrogenesis of bovine mesenchymal stem cells. 2012; p. 229-38.
211. Cho H, Seo Y-K, Yoon H-H, Kim S-C, Kim S-M, Song K-Y. Neural stimulation on human bone marrow-derived mesenchymal stem cells by extremely low frequency electromagnetic fields. *Biotechnology Progress*. 2012; 28(5):1329-35. Crossref. PMID:22848041.
212. Park J-E, Seo Y-K, Yoon H-H, Kim C-W, Park J-K, Jeon S. Electromagnetic fields induce neural differentiation of human bone marrow derived mesenchymal stem cells via ROS mediated EGFR activation. *Neurochemistry International*. 2013; 62(4):418-24. Crossref. PMID:23411410.
213. Kaivosoja E, Sariola V, Chen Y, Kontinen YT. The effect of pulsed electromagnetic fields and dehydroepiandrosterone on viability and osteo-induction of human mesenchymal stem cells. *Journal of Tissue Engineering and Regenerative Medicine*. 2015; 9(1):31-40. Crossref. PMID:23038647.
214. Teven CM, Greives M, Natale RB, Su Y, Luo Q, He B-C, et al. Differentiation of osteoprogenitor cells is induced by high-frequency pulsed electromagnetic fields. *Journal of Craniofacial Surgery*. 2012; 23(2):586-93. Crossref. PMID:22446422.
215. Kang KS, Hong JM, Kang JA, Rhie J-W, Jeong YH, Cho D-W. Regulation of osteogenic differentiation of human adipose-derived stem cells by controlling electromagnetic field conditions. *Experimental & Molecular Medicine*. 2013; 45(1):6. Crossref. PMID:23306704 PMCID:PMC3584658.
216. Baureus Koch CLM, Sommarin M, Persson BRR, Salford LG, Eberhardt JL. Interaction between weak low frequency magnetic fields and cell membranes. *Bioelectromagnetics*. 2003; 24(6):395-402. Crossref. PMID:12929158.
217. Sun X, McLamore E, Kishore V, Fites K, Slipchenko M, Porterfield DM, et al. Mechanical stretch induced calcium efflux from bone matrix stimulates osteoblasts. *Bone*. 2012; 50(3):581-91. Crossref. PMID:22227434.
218. Boonrungsiman S, Gentleman E, Carzaniga R, Evans ND, McComb DW. The role of intracellular calcium phosphate in osteoblast-mediated bone apatite formation. *Proceedings of the National Academy of Sciences of the United States of America*. 2012; 109(35):14170-5. Crossref. PMID:22879397 PMCID:PMC3435222.
219. Luo F, Hou T, Zhang Z, Xie Z, Wu X, Xu J. Effects of pulsed electromagnetic field frequencies on the osteogenic differentiation of human mesenchymal stem cells. *Orthopedics*. 2012; 35(4):526-31. Crossref. PMID:22495854.
220. Zhang X, Zhang J, Qu X, Wen J. Effects of different extremely low-frequency electromagnetic fields on osteoblasts. *Electromagnetic Biology and Medicine*. 2007; 26(3):167-77. Crossref. PMID:17886004.
221. Chang K, Chang WH-S, Wu M-L, and Shih C. Effects of different intensities of extremely low frequency pulsed electromagnetic fields on formation of osteoclast-like cells. *Bioelectromagnetics*. 2003; 24(6):431-9. Crossref. PMID:12929162.
222. Ferroni L, Tocco I, De Pieri A, Menarin M, Fermi E, Piattelli A. Pulsed magnetic therapy increases osteogenic differentiation of mesenchymal stem cells only if they are pre-committed. *Life Sciences*. 2016; 152:44-51. Crossref. PMID:26979772.
223. Ghazanfari S, Tafazzoli-Shadpour M, Shokrgozar MA. Effects of cyclic stretch on proliferation of mesenchymal stem cells and their differentiation to smooth muscle cells. *Biochemical and Biophysical Research Communications*. 2009; 388(3):601-5. Crossref. PMID:19695226.
224. Xu T, Yang K, You H, Chen A, Wang J, Xu K, Gong C, Shao J, Ma Z, Guo F, Qi, J. Regulation of PTHrP expression by cyclic mechanical strain in postnatal growth plate chondrocytes. *Bone*. 2013; 56(2):304-11. Crossref. PMID:23831868.

225. Subramony SD, Su A, Yeager K, Lu HH. Combined effects of chemical priming and mechanical stimulation on mesenchymal stem cell differentiation on nanofiber scaffolds. *Journal of Biomechanics*. 2014; 47(9):2189-96. Crossref. PMID:24267271 PMCID:PMC4058785.
226. Choi JW, Choi BH, Park SH, Pai KS, Li TZ, Min BH, Park SR. Mechanical stimulation by ultrasound enhances chondrogenic differentiation of mesenchymal stem cells in a fibrin-hyaluronic acid hydrogel. *Artificial Organs*. 2013; 37(7):648-55. Crossref. PMID:23495957.
227. Ghezzi CE, Marelli B, Donelli I, Alessandrino A, Freddi G, Nazhat SN. The role of physiological mechanical cues on mesenchymal stem cell differentiation in an airway tract-like dense collagen-silk fibroin construct. *Biomaterials*. 2014; 35(24):6236-47. Crossref. PMID:24818890.
228. Choi Y, Lee DH, Seo Y. Stimulation of Neural Differentiation in Human Bone Marrow Mesenchymal Stem Cells by Extremely Low-Frequency Electromagnetic Fields Incorporated with MNPs. *Applied Biochemistry and Biotechnology*. 2014; 174(4):1233-45. Crossref. PMID:25099373.